

Natural-origin materials for tissue engineering and regenerative medicine

Simone S Silva^{1,2}, Emanuel M Fernandes^{1,2}, Joana Silva-Correia^{1,2}, Sandra Pina^{1,2},
Sílvia Vieira^{1,2}, Joaquim M Oliveira^{1,2}, Rui L Reis^{1,2}

¹3B's Research Group – Biomaterials, Biodegradables and Biomimetics, University of Minho, Headquarters of the European Institute of Excellence on Tissue Engineering and Regenerative Medicine, AvePark- Parque de Ciência e Tecnologia, 4805-017 Barco, Guimarães, Portugal.

²ICVS/3B's – PT Government Associated Laboratory, Braga/Guimarães, Portugal.

E-mail addresses: simonesilva@dep.uminho.pt (Simone S. Silva);
efernandes@dep.uminho.pt (Emanuel M Fernandes); joana.correia@dep.uminho.pt
(Joana Silva-Correia); sandra.pina@dep.uminho.pt (Sandra Pina);
silvia.vieira@dep.uminho.pt (Sílvia Vieira); miguel.oliveira@dep.uminho.pt (Joaquim
M. Oliveira); rgreis@dep.uminho.pt (Rui L. Reis).

1. Introduction

2. Polysaccharides and proteins

2.1. Polysaccharides

2.1.1. Algae polysaccharides

2.1.2. Animal polysaccharides

2.1.3. Plant polysaccharides

2.1.4. Microbial polysaccharides

2.2. Proteins

3. Bioactive agents and growth factors

4. Strategies for tissue engineering

4.1. Membranes

4.2. Micro/nanoparticles

4.3. Scaffolds

4.4. Hydrogel materials

5. Biomedical/Biotechnological applications

5.1 Cell encapsulation

5.1.1. Immunisation and drug delivery

5.1.2. Storage and Transport

5.1.3. Cell delivery

5.2 Application in Intervertebral Disc Regeneration

6. Final remarks and future trends

Acknowledgement

References

Abstract

Recent advances in tissue engineering and regenerative medicine have shown that combining biomaterials, cells, and bioactive molecules are important to promote the regeneration of damaged tissues or as therapeutic systems. Natural origin polymers have been used as matrices in such applications due to their biocompatibility and biodegradability. This chapter provides an up-to-date review on the most promising natural biopolymers, focused on polysaccharides and proteins, their properties and applications. Membranes, micro/ nanoparticles, scaffolds, and hydrogels as biomimetic strategies for tissue engineering and processing are described, along with the use of bioactive molecules and growth factors to improve tissue regeneration potential. Finally, current biomedical applications are also presented.

Keywords: Cell encapsulation; cryopreservation; composites; growth factors; hydrogels; hypothermal preservations; immunoisolation; membranes; micro/nanoparticles; natural polymers; proteins; regenerative medicine; scaffolds; tissue engineering.

LIST OF ABBREVIATIONS

ACE – Acemannan

AF- Annulus fibrosus

ALP- Alkaline phosphatase

BC - Bacterial cellulose

BMPs - Bone morphogenetic proteins

CA - Carrageenan

CaP- Calcium phosphates

CAV- Chitosan/aloe vera

CH/CS NPs - Chitosan-chondroitin sulfate nanoparticles

CS - Chondroitin sulfate

2D - Two-dimensional

3D - Three-dimensional

Da- Daltons

DS- Dermatan sulfate

ECM - Extracellular matrix
EGF- Epidermal growth factor
ESCs - Mouse embryonic stem cells
FGF – Fibroblast growth factor
GAGs- Glycosaminoglycans
GelMA- Methacrylated gelatin
GF- Growth factor
GG- Gellan gum
GG-MA- Methacrylated gellan gum
hBMSCs- Human bone marrow mesenchymal stem cells
hMSCs- Human mesenchymal stem cells
HAp -Hydroxyapatite
HA – Hyaluronic acid
HS- Heparan sulfate
HUVECs - Human umbilical vein endothelial cells
IGF- Insulin growth factor
IL- Ionic liquid
IVD- Intervertebral disc
MWCO - Molecular weight cut-off
MSCs - Mesenchymal stem cells
NP- Nucleus pulposus
PDGF- Platelet-derived growth factor
PDMS – Poly(dimethylsiloxane)
PEG – Polyethylene glycol
PL- Platelet lysate
PLGA- Poly(lactic-co-glycolic acid)
PRP- Platelet-rich-plasma
PVP- Polyvinylpyrrolidone
RP - rapid prototyping
TE – Tissue Engineering
TERM- Tissue engineering and regenerative medicine
TGF- Transforming growth factor
TMTD - Triazole–thiomorpholine dioxide
SF- Silk fibroin

SiNP - Silica nanoparticles

SRP- Stimulus-responsive polymers

PNIPAAm - Poly(N-isopropylacrylamide)

VEGF – Vascular endothelial growth factor

1. Introduction

Tissue engineering and regenerative medicine (TERM) is a multidisciplinary field that combines three fundamental tools, namely biomaterials, adequate cells and signaling molecules aiming to replace and regenerate damaged tissues. Current efforts focus on developing strategies that include 3D-based matrices to support cells, promoting their differentiation and proliferation envisioning the formation of new tissues. Such approaches will provide the production of hybrid constructs with adequate structural and mechanical properties that behave as bioresorbable temporary implants to induce the tissue regeneration or replace failing or malfunctioning organs.

Several materials have been proposed to be used in the processing of scaffolds, namely natural biodegradable polymers. Natural origin polymers derived from renewable resources, namely from algae, animal, plant, and microorganisms, offer the advantage of being similar to biological macromolecules, which biological environment is prepared to recognize and to deal metabolically with. Due to their similarity with the extracellular matrix (ECM), natural polymers may also avoid the stimulation of chronic inflammation or immunological reactions and toxicity, often detected with synthetic polymers. Therefore, the features of the natural polymers are the key players for designing therapeutic systems that can be used to deliver drugs or bioactive compounds efficiently to treat diseases or even to bioengineer functional tissues for organ replacement. This chapter provides an up-to-date review on the most promising natural origin polymers, namely polysaccharides (*e.g.* alginate, cellulose, chitosan) and proteins (*e.g.* collagen, silk fibroin, elastin) that have been proposed to be used in tissue engineering (TE) strategies, with some emphasis on their properties, and the strategies used for the processing such kind of materials into membranes, scaffolds and hydrogels. Moreover, materials containing cells and/or bioactive cells or even cell encapsulation into these materials that can be used in a non-invasive way are also discussed.

An overview of the properties, strategies and biomedical applications, namely cell encapsulation and intervertebral disc regeneration of natural polymers herein addressed is presented in Figure 1.

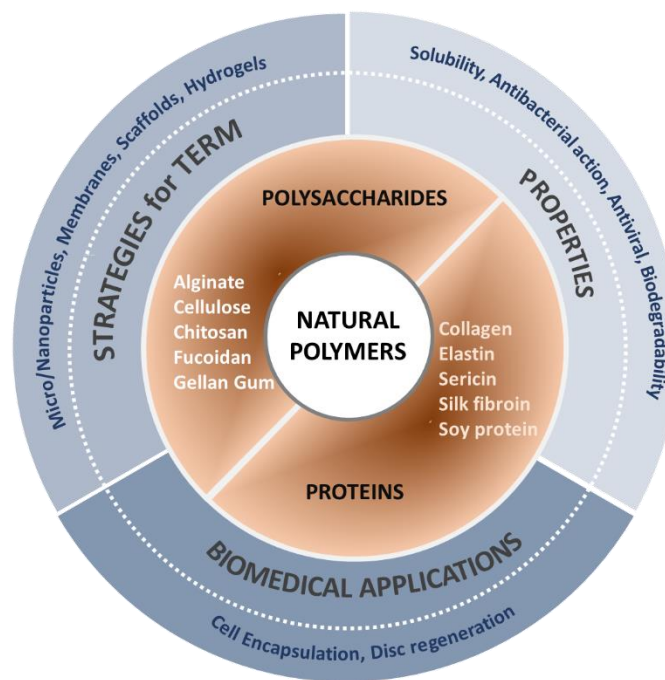


Figure 1: Overview of the properties, strategies and biomedical applications of natural polysaccharides and proteins for TERM.

2. Polysaccharides and proteins

2.1. Polysaccharides

Polysaccharides consist of repeating monosaccharide units linked by glycosidic bonds. Besides, polysaccharides can be obtained or synthesized from different abundant renewable resources in nature, namely algae (*e.g.* alginate, agarose, carrageenan, fucoidan, and ulvan), plant (acemannan, cellulose, and starch), microbial (bacterial cellulose, dextran and gellan gum) and animals (*e.g.* chitin/chitosan, chondroitin sulphate, glycosaminoglycans, heparin and hyaluronan).¹ As natural biopolymers polysaccharides are biodegradable, biocompatible and non-toxic.^{1b} Furthermore, polysaccharides have a great number of reactive groups such as hydroxyl, carboxyl, and amino groups that make them easily chemically modified or physically blended.² These characteristics together with their intrinsic and biological properties suggested that polysaccharides are promising biomaterials. The physicochemical and biological properties of the mentioned polysaccharides are reviewed in the following sections.

2.1.1. Algae polysaccharides

Alginate is a linear polymer of $\beta(1\rightarrow4)$ -linked D-mannuronic acid and $\alpha(1\rightarrow4)$ -linked L-guluronic acid.³ Alginate is present in the cell wall of brown algae as different salt forms of alginic acid, namely calcium, magnesium and sodium salts.³⁻⁴ Gelation is an important feature of alginates, and it depends on its molecular weight, molecular structure, and gelation agent concentration (*e.g.* calcium ions concentration).^{2c, 3} For instance, alginate gels can be formed through hydrogen bonding at low pH or by ionic interaction with di- or polyvalent cations.^{2c, 5} Besides controllable gelation, alginate is recognized by its biocompatibility, immunogenicity, and low toxicity. In TE, alginate is used in the development of hydrogels, micro/nanoparticles, and beads, for various applications including wound healing, protein delivery, and cell encapsulation.^{3, 5} However, some drawbacks of alginate have been evidenced such as uncontrollable degradation profiles, inadequate mechanical properties and lack of cell recognition signals.^{2a} Nevertheless, the application of conventional chemical modification on alginate including oxidation, graft copolymerization, sulfation, and esterification can enhance or tailor its properties, as reviewed previously.^{2a, 2b}

Agarose is a linear polysaccharide found in seaweeds composed of $(1\rightarrow3)$ - β -D-galactopyranose- $(1\rightarrow4)$ -3,6-anhydro- β -L-galactopyranose unit. This neutral polysaccharide forms thermoreversible gels when solubilized in water.⁶ In biomedical applications, the thermosensitive character of agarose has been combined with other biomolecules as chitosan, gelatin, and fibrin.⁷ These approaches have been utilized in the formation of hydrogels that can be applied directly at the desired site; and in the fabrication of different bioengineered tissues, including skin and peripheral nerve.^{7b, 8}

Carrageenan (CAs) are highly sulfated linear polysaccharides, present in red algae, with alternating repeating 3,6-anhydro-D-galactose and β -D-galactose 4-sulfated units. The number of sulfate groups per disaccharide unit in the structure determines the type of CAs that can be kappa (κ), iota (ι) and lambda (λ) distinguished in the presence of one, two or three sulfate groups, respectively. One of its main properties relies on the ability to form thermoreversible gels at room temperature in the presence of appropriate counterions. Recently, κ -CA-based materials have gained wide interest for TE applications namely as an injectable matrix for the delivery of living cells, bone regeneration, designing drug

delivery systems due to their intrinsic thixotropic behavior, the versatility of processing and resemblance to GAGs.⁹ Moreover, the presence of functional groups (i.e. hydroxyl and sulphate groups) allows them to be easily modified, generating derivatives with improved properties and better stability.^{9a, 9c}

Fucoidan is an anionic sulfated polysaccharide extracted from marine brown algae. Structurally, fucoidan is composed of a backbone of (1→3)- and (1→4)-linked α -l-fucopyranose residues; that may be organized in stretches of (1→3)- α -fucan or of alternating α (1→3)- and α (1→4)-bonded l-fucopyranose residues.¹⁰ Moreover, fucoidan is a water-soluble polymer with several biological properties for TE approaches including anti-inflammatory, anti-oxidative, anticoagulant, antithrombotic, anti-tumor and reducing blood glucose.¹¹ In fact, the ability to combine fucoidan with other polymers like chitosan and gelatin and/or inorganic components, such as tricalcium phosphate and hydroxyapatite (HAp), has been explored for the production of matrices (e.g. micro/nanoparticles, fibers, and films) useful for oral delivery, burn wound healing and bone TE.

Ulvan is a sulphated polysaccharide isolated from green algae belonging to *Ulva sp.*¹² The composition of ulvan is variable, but rhamnose, uronic acid, xylose and sulphate groups are the main components of this polymer.¹³ Recently, ulvan has been suggested as a starting material for designing many structures, namely nanofibers, membranes, hydrogels and 3D porous materials¹³⁻¹⁴. The applicability of these matrices may range from wound dressing to drug delivery and cell delivery. Moreover, ulvan can be easily modified through its functional groups (carboxyl, hydroxyl and sulphate groups) to achieve the needs for an envisaged biomedical application.

2.1.2. Animal polysaccharides

Chitin and chitosan are polysaccharides with great structural possibilities for the creation of the derivatives and matrices for different biomedical applications, including TERM.¹⁵ **Chitin** (β -(1-4)-poly-*N*-acetyl-*D*-glucosamine) can be found in shells of crustaceans such as crabs and shrimps.^{15a} Furthermore, chitin can also be extracted from endoskeletons of cephalopods. Depending on its source, chitin can be characterized by α - and β -form, distinguished by strong and weak inter- and intramolecular bonds, respectively.¹⁶ This polymer has appealing properties namely biocompatibility, tumor cell growth suppression, acceleration of wound healing and antimicrobial activity.^{1a, 15a} These

properties have encouraged the production of chitin-containing products such as artificial blood vessels, tumor inhibitors, vascular implants and dressing for burns. Despite the promising biomedical use of chitin, its application has been limited due to its strong inter- and intra-molecular bonding between the polymer chain, which results in a lack of solubility in water and common organic solvents^{1a}. Nevertheless, recent studies proposed that ionic liquids (ILs), defined as organic salts like 1-butyl-3-methylimidazolium acetate,¹⁷ can be used not only as a solvent but also as reaction media of some polysaccharides, including chitin,¹⁸ chitosan,¹⁹ cellulose²⁰ and silk fibroin.²¹ In particular, chitin/IL solutions can be used in the preparation of 2D and 3D-based matrices namely gels, films, sponges and micro/nanoparticles. Given the performance of the resulting chitin-based matrices, they may be applied in drug delivery, bone regeneration, gene delivery, and skin repair.^{18a, 18c, 22}

Chitosan is the N-deacetylated derivative of chitin.^{15a} Chitosan is recognized as an important biomaterial due to its intrinsic properties namely its polyelectrolyte and cationic nature, mucoadhesion, hemostatic action, film-forming ability, biodegradability and anti-microbial action.^{1a} Moreover, chitosan is a versatile raw material for the designing of 2D and 3D-based matrices such as membranes, fibers, particles and composites at micro/nano level for applications in bone, skin and cartilage TE.^{15a} The combination of chitosan with other polymers (natural or synthetic ones) and/or proteins are approaches frequently used to create blends and composites.²³ Besides, chitosan derivatives have been developed using several chemical and physical procedures. These chitosan-based materials have suitable properties and functionalities for biomedical purposes, for instance, dermal substitutes, cancer diagnosis, drug delivery and gene therapy.^{15a} With the rise of nanotechnology, chitosan, together with other macromolecules, has also been fabricated into various bionanocomposites, providing alternative applications in regenerative medicine and drug delivery vesicles.^{5, 24}

Glycosaminoglycans (GAGs) are linear, complex and polydisperse natural polysaccharides, composed of a repeating disaccharide unit formed by a hexose and a hexosamine. GAGs can regulate the action of proteins essential to bone and skin regeneration and modulate the biological performance of skin and bone precursor cells and their subsequent differentiation and gene expression. However, the precise action of GAGs varies according to their structural composition mainly on the degree of sulfation and polymer length. The sulfated GAGs such as chondroitin sulfate (CS), dermatan sulfate (DS), and heparan sulfate (HS) represent a group of bioactive polysaccharides

derived from animals. The characteristics of the mentioned GAGs together with their defined physical properties make them interesting material for TE. For instance, CS has functions in wound repair, response to infection, growth factor signaling, morphogenesis, and cell division, in addition to their conventional structural roles.²⁵ Moreover, many studies using shark-derived CS suggests that this type of CS may reduce allergic response and have an anti-allergic effect. CS and DS chains have interesting functions in central nervous system development, wound repair, infection, growth factor signaling, and cell division.²⁵

Hyaluronic acid or hyaluronan (HA), is a water-soluble polysaccharide formed by a structure linear with a repeating disaccharide structure composed by α -1,4-D-glucuronic acid and β -1,3-N-acetyl glucosamine bonds. As a biomaterial, HA is suitable for a wide range of applications due to its biodegradability, biocompatibility, viscoelastic properties, nontoxicity, and nonimmunogenicity. Nonetheless, HA has low shape stability and poor mechanical properties. So, usually, HA is a key component in the preparation of 2D and 3D matrices such as membranes, hydrogels, and scaffolds that can be either chemically or physically modified or degraded controllably.²⁶ Hence, HA and HA-based materials serve as excellent tools for many biomedical needs such as orthopaedic, cardiovascular, pharmacologic and oncologic applications.²⁶⁻²⁷

2.1.3. *Plant polysaccharides*

Acemannan (ACE) is a β (1 \rightarrow 4)-acetylated polymannose present in the inner leaf gel of Aloe vera plant, a medicinal plant.²⁸ ACE has been described by its multifunctional properties such as immunomodulatory activity, antiviral, antioxidant and antibacterial actions.²⁸⁻²⁹ Therefore, ACE acts as a bioactive molecule, exerting an immunostimulatory effect by activating macrophages,³⁰ induction of VEGF expression and wound healing actions.^{29, 31} Recent studies demonstrated that ACE stimulated gingival fibroblast proliferation³², dental pulp fibroblast proliferation,³³ periodontal tissue regeneration³⁴ and bone marrow stromal cell proliferation and differentiation *in vitro*.³¹ These works suggested ACE as a therapeutic agent for tissue repair. However, further research studies are needed to validate and explain the action mechanism of ACE in healing.

Cellulose, the most abundant polysaccharide in nature, is constituted by β (1 \rightarrow 4) linked-D-glucopyranose units. The polymeric chains are packed through hydrogen bonds and van der Waals forces forming fibrous structures called microfibrils. These nano structured

microfibrils with high structural strength and stiffness. This crystalline part is named nanowhiskers. Despite its great availability, cellulose has a high crystallinity degree and rigid intra/intermolecular hydrogen bonds which result in its insolubility in most solvents. To overcome these drawbacks, many chemical functionalizations based on hydroxyl groups, as e.g. esterification, graft copolymerization, and selective oxidation has been used to generate different cellulose derivatives.^{2a} For instance, oxidized cellulose is used as an excellent hemostatic material in various surgical procedures; while other cellulose derivatives (in hydrogel and aerogel form) have been used in wound healing, 3D-cell culture, and drug delivery systems.³⁵ Besides, recent advances on the homogeneous modification and functionalization of cellulose have also been achieved using ILs, opening novel possibilities for its biomedical applications.²⁰ For example, Park *et al.* produced cellulose/chitosan composite nanofibers using 1-ethyl-3-methylimidazolium acetate, which could be used as an antibacterial reagent to treat skin ulcers.³⁶ On a composite perspective, the use of cellulose crystals (*e.g.* nanowhiskers) is based on their high stiffness, being relevant as a reinforcement strategy in several systems such as hydrogels systems.^{27b, 35}

Starch is a biopolymer composed of two major components, namely α -amylose and amylopectin. Starch can be found in many plant sources, such as corn, rice, potato, and wheat.³⁷ Depending on the source, the physico-chemical and functional properties of starch can vary. Chemical and physical modifications, and/or even combinations with other natural or synthetic polymers are some of the approaches applied onto starch to overcome its lack of processability. In TE, the starch-based materials *e.g.* 3D scaffolds, micro/nanoparticles, bone cement, and hydrogels, have been used as a carrier for controlled release of drugs.

2.1.4. Microbial polysaccharides

Bacterial cellulose (BC) can be produced by *Gluconacetobacter xylinus* or *Acetobacter xylinum*.³⁸ Although its similar molecular formula to plant origin cellulose, BC is characterized by a crystalline nano-fibrillar structure which creates a large surface area that can retain a large amount of liquid.^{38a, 38c} BC has also been proposed to be used as an effective wound material due to its unique properties such as versatility, moldability *in situ*, biocompatibility, high water-holding ability, cost effect production and high mechanical strength in the wet state.^{38b, 38c, 39} Furthermore, BC is used as wound dressing

composites with collagen type I,⁴⁰ chitosan^{23a, 41} and aloe vera.⁴² BC could be used in the production of scaffolds, transdermal applications and as a pharmaceutical excipient in drug delivery systems.^{35, 43} In transdermal drug delivery, for instance, BC membranes could work bilaterally, both to deliver drug and absorb exudates.

Dextran is a biodegradable neutral bacterial exopolysaccharide consisting of repeating glucose subunits. Dextran is soluble in water and organic solvents, and this feature can be used in the preparation of different structures through blending dextran with bioactive agents or hydrophobic polymers. For instance, the interest in dextran hydrogels for soft TE has increased due to their great biocompatibility, the capability to reduce nonspecific protein adsorption and cell attachment. However, these properties are not sufficient for dextran hydrogels to fulfill their role to act as a TE scaffold. The conjugation of bioactive moieties such as RGD on dextran could facilitate tissue growth and regeneration.⁴⁴ Moreover, dextran can also be chemically modified to form spherical, tubular and 3D network structures.⁴⁵ Dextran has also been applied in nanomedicine. Dextran nanoparticles have superior aqueous solubility, high cargo capacity and intrinsic viscosity, and short storage period.⁴⁶ Therefore, the features of dextran made it suitable as nanodrug carrier, cell imaging system, and nanobiosensor.

Gellan gum (GG) is an anionic extracellular polysaccharide, composed by approximately, 60% glucose, 20% glucuronic acid, and 20% rhamnose as a repeating unit, and two acyl groups, acetate and glycerate bound to glucose residue adjacent to glucuronic. GG is recognized as a thermally reversible gel with excellent stability and high gel strength. However, in its high acyl form, GG produces transparent, soft, elastic and flexible gels, whereas the low acyl form results in brittle gels. These features have stimulated different approaches to use it as injectable hydrogels to regenerate and repair the damaged cartilage,⁴⁷ and chemically modified for intervertebral disc (IVD) regeneration⁴⁸.

2.2. Proteins

Proteins are one of the versatile groups of macromolecules in living systems and play important functions in almost all biological processes. Proteins have also been used for the development of innovative materials for biomedical purposes mainly due to their (i) availability on a large scale and low cost; (ii) biodegradability since their degradation products are composed of amino acids that can be resorbed as nutrients; (iii) chemical

reactivity; and (iv) excellent biocompatibility. Given their unique properties, efforts have been expended in developing protein-based materials including films, capsules, foams, scaffolds, composites, and gels, through their association or not with bioactive compounds. These matrices have gained prominence as drug delivery systems, biosensors, and scaffolds for tissue regeneration. Moreover, the design approaches such as genetic engineering can be used for the synthesis of protein-engineered biomaterials, tailoring their properties (*e.g.* cell adhesion, elasticity, and biodegradability), and reducing the problems associated with those obtained from natural sources.

The features of the most promising proteins, namely collagen, gelatin, elastin, silk fibroin, sericin and soy protein used for TERM are described in the following paragraphs.

Collagen and gelatin

Collagen is the most abundant protein present in mammalian tissues (cornea, blood vessels, skin, cartilage, bone, tendon, and ligament) and is also the main component of the ECM. Gelatin is the partially hydrolysed form of collagen. Although sources of collagen and gelatin are bovine and porcine skin, recent studies have been shown their extraction from marine sources (*e.g.* marine sponges, fish skin) using simple protocols.¹⁶ Both collagen and gelatin are the most preferred ECM proteins used in TE. They can be processed into fibers, films, and foams to engineer many tissues such as bone, cartilage, ligament, nerve and heart.⁴⁹ Depending on the biomedical purpose, improvement of the physical, chemical and biological properties of collagen can be achieved through its combination with other polymers. Similar to collagen, the use of gelatin in TE has been correlated with its appealing features such as cell-adhesive structure, low cost, and biocompatibility. Gelatin can be processed as composite scaffolds, nanoparticles, employed as a size-controllable porogen, and acted as surface coating agent.⁵⁰ Recent research has shown the proficiency of methacrylated gelatin (GelMA) for bioprinting and micro-structured patterned applications. The derived structures are suitable for bone, cartilage, cardiac, vascular tissues, drug, and gene delivery.⁵¹

Elastin is a vital protein component of the ECM present in many mammalian tissues, which require elasticity as part of their function,⁵² including vasculature, skin and lungs. Mature elastin is an insoluble polymer composed of several tropoelastin molecules covalently bound to each other by cross-links. The nature of elastin itself has hindered the study of its properties and structure, mainly due to its insolubility in water and

backbone mobility. Elastin has inherent signaling properties that promote diverse responses, including chemotaxis, cell growth, and tissue homeostasis. Using the benefits effects of these characteristics, elastin and derivatives (tropoelastin and elastin derived peptides) can be used in the production of elastin-based materials and as surface coatings for polymers in order to improve cell adhesion and function on tissue engineered products. Elastin-like macromolecules are genetically engineered materials rooted in the repeating sequence of natural elastin.⁵³ They can be synthesized with a high degree of specificity and control, which is feasible by chemical methods. In fact, recombinant elastin-like polypeptides (ELPs) can be assembled into 3D matrices with tailored mechanical and thermal properties as well as unique functionalization opportunities using both enzymatic and genetic ways. Besides, incorporation of non-natural elements and inorganic materials in elastin-based materials could extend their application range, namely in diagnostic imaging and target therapeutic delivery.⁵⁴

Silk are a class of proteins containing fibroin (70–80%), the structural protein of silk fibers, and sericin (20–30%), the water-soluble glue-like protein that encased fibroin fibers. **Silk fibroin** (SF) is composed by glycine, alanine, and serine in different percentages. SF fibers are obtained from diverse sources such as non- and mulberry silkworm *Bombyx mori*, insects, and spiders.⁵⁵ SF possess good biocompatibility, elasticity, toughness, suitable mechanical properties and biodegradability with controllable degradation rates, make it a good biomaterial for TERM. SF is rich in β -sheet structures owing to hydrophobic domains thus influence its mechanical properties, biodegradation rate and the ability to support the cell adhesion and differentiation of MSCs Extensive studies have been carried out on the processing, blending and/or chemical modification of SF. It has also been combined with biomacromolecules as *e.g.* chitosan to form membranes, scaffolds, composites, micro/nanoparticles, nanofibers and hydrogels and/or with inorganic components like calcium phosphate (CaP) and HAp to generate composites.⁵⁶ These approaches have shown the benefits effects of SF-based structures for skin cartilage, bone, and ligament TE.

Sericin comprises a variable amino acid compositions such as serine, glycine, glutamic acid, aspartic acid, threonine, and tyrosine. This protein is considered a waste during silk processing. However, sericin exhibits attractive bioactive properties such as antioxidant, moisturizing ability, pH responsiveness and mitogenic effect on mammalian cells,⁵⁷ with potential applications in regenerative medicine. Sericin-based biomaterials such as sponges, hydrogels, micro/nanoparticles, composites, and films produced by ethanol

precipitation, crosslinking or blending with other polymers and/or with inorganic components⁵⁸ have been employed as dermal reconstruction and wound dressing for skin tissue repair, bone TE, and drug delivery.⁵⁹

Soy protein is a globular protein isolated from soybeans. About 90-95% of the soy is a storage protein, with two subunits, namely 35% conglycinin (7S) and 52% glycinin (11S). Soy protein has advantages over the various types of natural proteins employed for biomedical applications, namely its low price, non-animal origin and relatively long storage time, and stability. Besides, the combination of its properties with a similarity to tissue constituents and a reduced susceptibility to thermal degradation makes soy protein a plant-derived macromolecule of interest in the biomedical field.⁶⁰ Membranes, fibers, microparticles and thermoplastics-based soy materials have been developed associating soy protein with other proteins (*e.g.* wheat gluten,⁶¹ casein⁶²), polysaccharides, such as cellulose,⁶³ chitosan,⁶⁴ and synthetic materials. The resulting matrices are helpful for tissue regeneration,⁶⁵ drug delivery system, and wound dressings.^{1a, 64b}

2.3. Bioactive agents and growth factors

One of the significant challenges in TERM involves the production of matrices associated with bioactive signaling molecules that can promote cell adhesion, proliferation, differentiation, and metabolic activity for the *in vivo* regeneration process. These molecules are grouped in mitogens (that stimulate cell division), growth factors (with proliferation-inducing effects), and morphogens (that control generation of tissue form). In particular, growth factors (GFs) are signaling molecules capable of instructing cells, stimulating cellular growth, proliferation, healing and cellular differentiation in a biological environment. Given the critical role of GFs stability in cellular responses, of *in vivo* situations, natural polymers- based systems are good platforms as bioactive delivery substrates. These matrices could affect not only the encapsulation efficiency of the bioactive agents but also cell fate. Distinct strategies have been employed to prolong their release rate and increase their therapeutical effect in TE, namely (i) chemical immobilization of GFs into the polysaccharide- or protein-based matrices, and (ii) physical encapsulation of GFs in the delivery systems.⁶⁶ Examples of GFs and their carrier-based polymeric systems used in TE are presented in Table 1.

Platelet lysate (PL) has been increasingly explored in TERM as a natural and cost-effective resource of GFs and multiple proteins, and/or as a support for cell growth and differentiation. In fact, platelets have a wide range of cytokines such as the isoforms of

Insulin Growth Factor (IGF), Platelet-Derived Growth Factor (PDGF), Transforming Growth Factor (TGF), among others. Recent strategies for a controlled incorporation of PL have been developing using nanocoatings by layer-by-layer with marine origin polymers⁶⁷ (see Figure 2), and the production of biomimetic 3D hydrogel structure based on the assembly of chitosan-chondroitin sulfate nanoparticles (CH/CS NPs) carrying PLs.⁶⁷

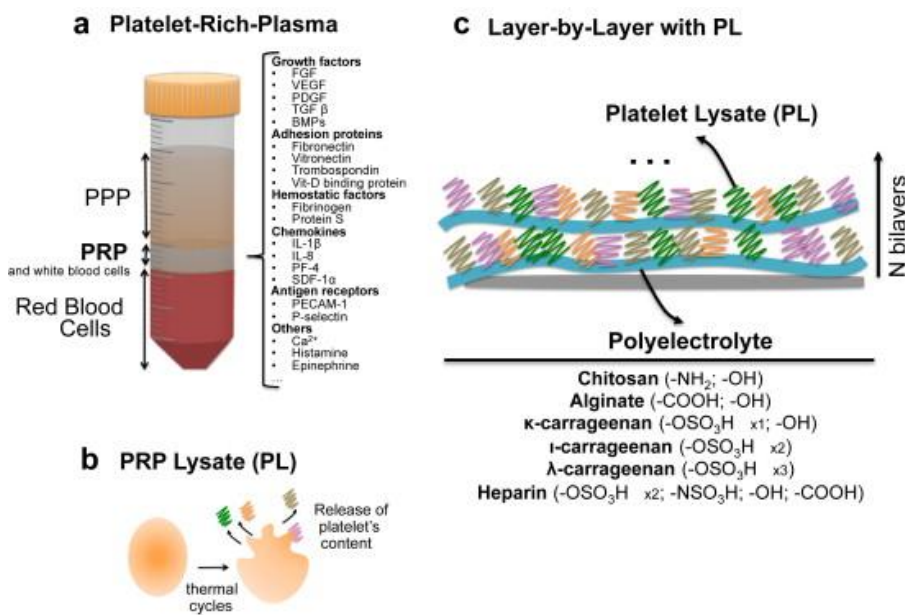


Figure 2. Main steps for the preparation of PL/Polysaccharides Layer-by-Layer assembled nanocoatings. a) Platelet isolation from human blood as Platelet-Rich-Plasma (PRP) and examples of bioactive proteins than can be found in the enriched protein cocktail; b) PL preparation: PRP activation by platelet disruption induced by thermal cycles for the release of the inner content and (c) Layer-by-Layer deposition combining PL with several PEs which respective functional groups and content are indicated. Adapted from Ref⁶⁷ with permission.

Table 1: Growth factors, their main functions and some examples of polymer-based carrier systems used in TE.

Growth factors	Main functions	Examples of polymer-based carrier systems	Ref
BMPs	Osteoblast cells differentiation and migration To induce MSCs to differentiate into bone.	Heparin-conjugated fibrin system	68
EGF	Regulation of epithelial cell growth, proliferation and differentiation	PLGA/gelatin hybrid nanofibrous scaffolds	69
FGF	Migration, proliferation and survival of endothelial cells	Gelatin sponge, Chitosan/fucoidan nanoparticles	24b, 70
IGF	Cell proliferation, inhibition of cell apoptosis	Collagen/GAG scaffold	71
NGF	Survival and proliferation of neural cells	Chitosan- β -glycerophosphate hydrogel	72
PDGF	Embryonic development, proliferation, migration, growth of endothelial cells	Gelatin hydrogels	73
TGF	Wound healing and increase cell proliferation and differentiation	Chitosan microspheres	74
VEGF	-Migration, proliferation and survival of endothelial cells. -Induce angiogenesis	Star-poly(ethylene glycol)-heparin hydrogel	75

Abbreviations: BMPs: Bone morphogenetic protein; EGF: Epidermal growth factor; PLGA: Poly(lactic-co-glycolic acid); FGF: Fibroblast growth factor; IGF: Insulin-like growth factor; NGF: Nerve growth factor; PDGF: Platelet-derived growth factor; TGF: Transforming growth factor; VEGF: Vascular endothelial growth factor.

3. Strategies for tissue engineering

Diverse strategies have been developed to engineer new tissues mimicking the natural tissue ECM to enhance cell-biomaterial interactions, and promote cell adhesion, proliferation, and differentiation ability. These strategies hold micro/nanoparticles, membranes, scaffolds, and hydrogels, with a specific design, controlled degradation rate, mechanical properties, and porosity for efficient gases, nutrients, and regulatory factors transport.

Conventional techniques such as foam replica method, solvent casting and particulate-leaching, freeze drying, gas foaming, and phase separation, are inexpensive and flexible to optimize physicochemical properties and have been used to produce structures. Rapid prototyping, supercritical fluid technology bioprinting, photolithography, microfluidics and electrospinning, as more sophisticated techniques, are also used for 3D structures and fibers, respectively, allowing the possibility of incorporating pharmaceutical agents. A brief description of such strategies is provided below.

Membranes

Membranes have been used in different TE applications, namely in wound healing, construction of drug delivery systems and diagnostic devices, due to its ease of manufacturing and self-application.^{1a, 76} Membranes can be produced using solvent casting with or without porogen, freeze-drying technique, spin casting, and electrospinning.⁷⁷ Solvent casting are the technique commonly used in the preparation of polymeric membranes, owing the advantage of producing large and constant surface areas. This method consists in the polymer dissolution in an appropriate solvent and subsequent solvent evaporation. Additionally, drugs or specific molecules can be incorporated during the dissolution of the polymer or even on the casted film. The membrane structure and its properties are influenced by many experimental factors such as choice of solvent and non-solvent, polymeric solution composition, and humidity. Furthermore, instead of using pure polymer, two or more polymers can be mixed to form blends which are useful in the production of membranes with desirable properties. Many polymeric membranes have been produced using polysaccharides, proteins or their combinations envisioning biomedical TE applications. For example, Silva *et al.* developed blended membranes composed by chitosan and aloe vera (CAV) using the solvent casting technique.^{15b} Results showed that the incorporation of AV into chitosan

provided blended membranes with better physical (roughness, degradation rate, wettability, mechanical properties) and cellular response (Figure 3) when compared to chitosan alone.

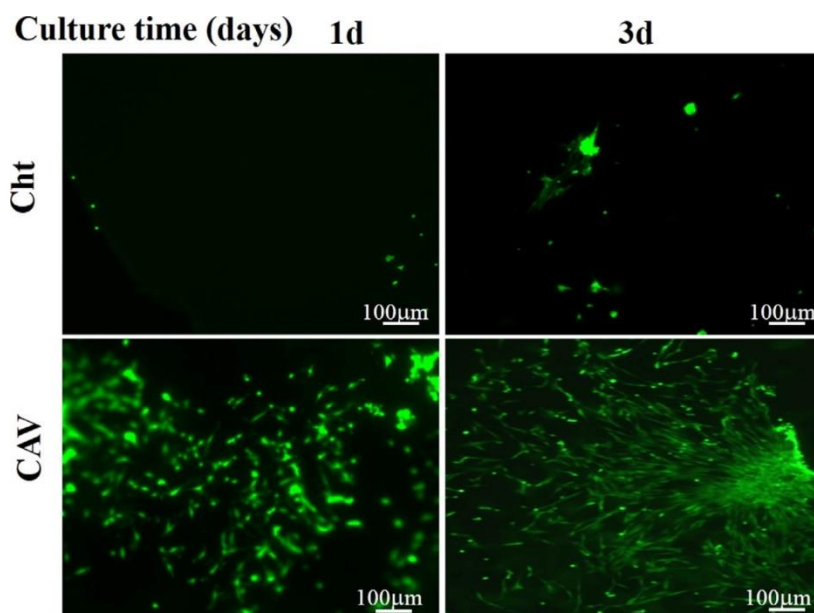


Figure 3: Calcein-AM staining of human dermal fibroblasts cells cultured for 1 and 3 days on the membranes (chitosan and chitosan/aloe vera, CAV). Adapted from Ref ^{15b} with permission.

The membranes surface properties, as *e.g.* roughness, wettability and surface energy, are important parameters that influence their biomedical application. Therefore, modification of the membrane surface is often needed to enhance the interaction of such material with the host or biological fluid and suppress the immune response. Various methods have been employed for modifying polymer surfaces including chemical modification, UV, gamma irradiation, and plasma surface modification. These modifications can determine the possible interactions of polymers with bioactive agents (*e.g.* growth factors, drugs). In plasma surface modification, the material is exposed to a partially ionized gas resulting in the formation radicals on the polymer surface that will modify the surface.^{1a, 78} Also, the activation of the membrane surface can be used to create smart surfaces, where the wettability can be responsive to the change of external variables.⁷⁹ For example, surface properties of membranes can be modulated in response to an external stimulus (*e.g.* pH or temperature), and this characteristic could be useful to modulate the release of drugs.

A similar effect can be achieved through grafting of the monomer by chemical initiators using free radical polymerization methods. In that case, surface bound stimulus responsive polymers (SRP) can also be incorporated into membranes to create thermosensitive membranes.

3.1. Micro- and nanoparticles

Micro- and nanoparticles can be used in a large variety of TERM applications ranging from therapeutic delivery,⁸⁰ cardiovascular imaging,⁸¹ to *in vitro* diagnosis,⁸² incorporations in scaffolds or hydrogels,⁸³ or incorporated in biomaterials for the delivery of bioactive factors.^{83a}

Micro- and nanoparticles have properties that can make them more or less useful for different applications, with particle diameters usually ranging from 1 to 100 μm , and 1 to 100 nm, respectively. The nanoscale dimension has unique physicochemical properties, such as ultra-small size, large surface area, and high reactivity when compared to the conventional microsized particles.⁸⁴ Nanoparticles are functionalized or surface-modified by capping certain functional groups on their surfaces, with specific recognition chemical moieties and enhanced efficacy, while simultaneously reducing side effects, due to properties such as targeted localization in tumors and active cellular uptake.⁸⁵ Various morphologies have been used to prepare nanoparticles, including liposomes, nanospheres, nanocapsules, micelles, and dendrimers,^{80a, 86} which main characteristics are well documented in the literature.⁸⁷

Numerous micro- and nanoparticle compositions have been used in tissue engineering, including natural and synthetic polymers,^{23b, 88} inorganic/ceramic,⁸⁹ magnetic,⁹⁰ and gold nanoparticles.⁹¹ For example, chitosan nanoparticles loaded with dexamethasone presented a significant improvement of osteogenic differentiation of hMSCs for bone tissue regeneration.⁹² Park *et al.*⁹³ produced a hybrid composite scaffold using nanofibrous 2,2,6,6-tetramethylpiperidine-1-oxyl (TEMPO)-oxidized bacterial cellulose and HAP with enhanced cell adhesion, migration, growth, mineralization, and differentiation for bone tissue regeneration. In a different study, mesoporous silica-based nanoparticles incorporating bone-forming peptide derived from BMPs-7 were developed to obtain a system for osteogenic factor delivery.⁹⁴ Results showed high cell proliferation and alkaline phosphatase (ALP) activity, making it a potential candidate for bone regeneration and bioimplant coating applications. A study by Chen *et al.*⁹⁵ demonstrated that the presence of biphasic tricalcium phosphate microparticles incorporated into a

hyaluronic acid-*g*-chitosan-*g*-poly-*N*-isopropyl acrylamide hydrogel presented better cell proliferation and osteogenic differentiation than in the hydrogel alone.

Several methodologies have been presented in the literature for fabrication of polymeric micro/nanoparticles such as emulsification/solvent evaporation,⁹⁶ nanoprecipitation (also known as solvent displacement method),⁹⁷ salting out method,⁹⁸ ionic gelation,^{24a} spray drying,^{23b} sol-gel,⁹⁹ supercritical fluid technology,¹⁰⁰ microfluidics,¹⁰¹ and electrospraying.¹⁰² Manufacturing process should ideally allow the production of large quantities of particles with a narrow size distribution, with control of particle size, porosity and surface characteristics. Among them, the emulsion method is the most popular technique, which consists in the dispersion or dissolution of molecules into a polymer solution and emulsified to form micro/nano droplets that are further dried after solvent removal. However, the use of organic solvents is a disadvantage since it can lead to denaturation of protein-based drugs, thus increasing the variability in drug loading, encapsulation efficiency, size and surface morphology of nonhomogeneous particles.¹⁰³ To overcome these limitations, electrospraying technique has the potential to generate narrow size distributions of submicrometric particles, with limited agglomeration and high yields.¹⁰⁴ An example is presented in a study by Wang *et al.*⁹⁶ where it was fabricated a multiple-drug delivery system consisted of chitosan nanoparticles and polyvinylpyrrolidone (PVP) micro/nanocoating with core-shell structures, using ionic gelation and emulsion electrospray methods (Fig. 3). Results showed a successfully encapsulated dual model drugs, naproxen, and Rh.B, in the shell and core regions, with good release controllability.

Another processing method, often used by our group, for the fabrication of polymeric spheres, is based on the drop of the liquid precursor containing the polymer over superhydrophobic surfaces.¹⁰⁵ This method presents advantages over conventional emulsion and gelation techniques as the contact of the dispensed drops with an outer liquid environment is avoided. In addition, this process allows the encapsulation of living cells and/or therapeutic molecules for tissue engineering applications.¹⁰⁶

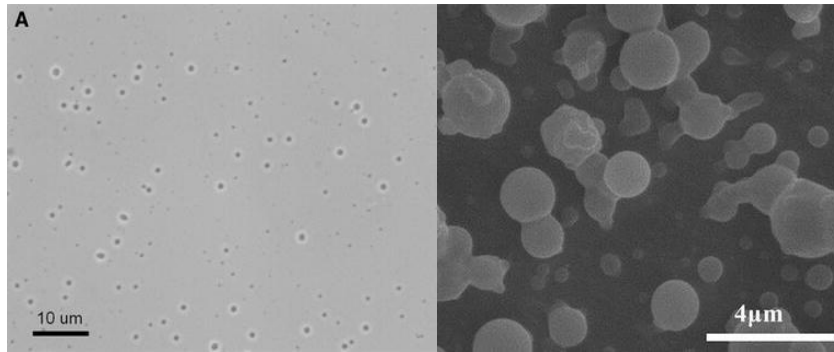


Figure 4: (A) An optical micrograph of the micro/nanoparticles, and (B) scanning electron micrograph of (naproxen/chitosan)/(Rh.B/PVP) core/shell micro/nanoparticles with naproxen/chitosan as the core and Rh.B/PVP as the shell. *Adapted from Ref. ⁹⁶ with permission.*

3.3. Scaffolds

Scaffolds are defined as porous 3D support structures of the surrounding tissues mimicking ECM, with basic requirements, namely: (i) to promote cell-biomaterial interactions, cell adhesion, growth, and migration; (ii) to facilitate transport of mass, nutrients, and regulatory factors to allow cell survival, proliferation, and differentiation; (iii) controlled degradation that approximates the rate of tissue regeneration under the culture conditions of interest; (iv) possess adequate mechanical properties necessary to temporarily offer structural support until the formation of new tissue occurs, like tensile strength and elasticity; and (v) to elicit a minimal degree of inflammation or toxicity *in vivo*.¹⁰⁷ Moreover, instead of simple injection of cells to the defects, scaffolds have the advantage of allowing cell transfer into a defect site and to restrict cell loss.¹⁰⁸

Scaffolds targeted for TE and regeneration have been developed using various natural and synthetic polymers, and bioactive inorganic materials, with specific pore size, porosity, surface-area-to-volume ratio, and crystallinity.¹⁰⁹ Composite materials combining a polymeric matrix and inorganic materials, as fillers, resulting in a single structure with significantly improved mechanical and biological properties, also appeared as a strategy for tissue engineering.¹¹⁰ Special interest has been attributed to nanocomposites for bone tissue engineering and regeneration due to the nanosized features of the fillers which can intensely improve the tissue bonding capacity of the

polymeric matrices, that the individual materials cannot attain thus allowing the production of better biomaterials.¹¹¹

Different technologies applied for scaffolds fabrication embrace foam replica method,¹¹² salt-leaching,¹¹³ freeze-drying,^{109, 114} phase separation,¹¹⁵ gas foaming,¹¹⁶ supercritical fluid,¹¹⁷ rapid prototyping,²² and electrospinning.¹¹⁸ Barbani *et al.*¹¹⁹ produced a gelatin/HAp nanocomposite scaffold with an elastic modulus similar to that of natural bone, using the freeze-drying technique. It was shown that HAp scaffolds supported the adhesion and proliferation of hMSCs onto the scaffolds. Recently, Martínez-Vázquez *et al.*¹²⁰ fabricated a 3D porous scaffold for bone regeneration and drug release capability, consisting of gelatine and Si-doped HAp through rapid prototyping technique, with adequate macroporosity for vascularization and microporosity that enables fluid exchange, as well possessing mechanical properties close to those of trabecular bone.

Our group has been developing mono- and bilayered porous structures for osteochondral tissue engineering applications. Yan *et al.*¹⁰⁹ developed a nanocomposite scaffold of SF and CaP using salt-leaching and freeze-drying methods, with superior mechanical properties and controllable porosity. The scaffolds supported new bone ingrowth, and no acute inflammatory was observed after 3 weeks of implantation. Based on their previous studies, the same authors fabricated bilayered scaffolds composed of an SF layer and an SF/nanoCaP layer, with different features (e.g. mechanical, chemical or morphology properties) for the simultaneous regeneration of the cartilage and the subchondral bone (Fig. 5).¹²¹ It was shown that the scaffolds integrated well with the host tissues and allowed tissue ingrowth when implanted in rabbit knee critical osteochondral defects. Furthermore, the bilayered scaffolds supported cartilage regeneration in the top silk layer and encouraged large amounts of subchondral bone ingrowth and angiogenesis in the bottom silk/nanoCaP layer.

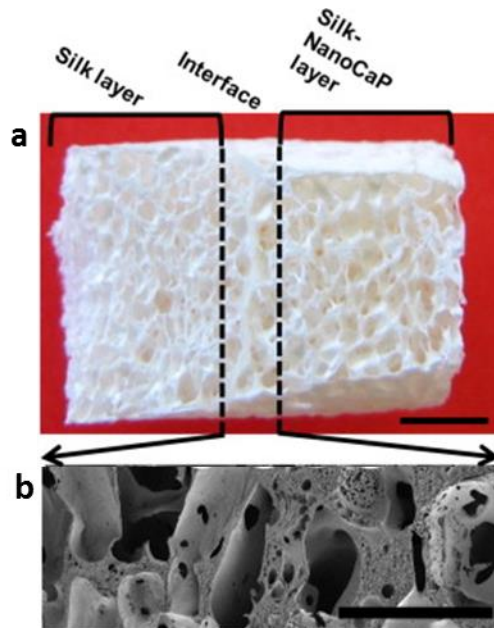


Figure 5: The interface of the bilayered scaffolds showing the different regions from the silk layer to the silk-nanoCaP layer: (a) Macroscopic image (scale bar: 3 mm), and (b) SEM image (scale bar: 500 μm). Adapted from Ref¹²¹ with permission.

3.4 Hydrogel materials

Hydrogel-based materials, often classified as natural or synthetic polymers networks, are pre-formed by chemical or physical crosslinking of water-soluble precursors.¹²² This class of biomaterials is an attractive candidate for building 3D structures that resemble the physical characteristics of the ECM because of their high water content, viscoelastic nature, and the easy diffusion of bio-macromolecules.¹²²⁻¹²³ Hydrogels are polymer networks extensively swollen with water held together by (i) primary covalent crosslinks; (ii) hydrogen bonds; (iii) ionic forces; (iv) affinity or “biorecognition” interactions; (v) physical entanglements of individual polymer chains; (vi) polymer crystallites; (vii) hydrophobic interactions; or (viii) a combination of two or more of the previous interactions.¹²⁴ Among them, naturally derived polymers recently used in hydrogel structures include collagen type I,¹²⁵ alginate,¹²⁶ HA,^{27b, 127} chitosan,^{7a, 125b, 128} gelatin,^{126b, 128-129} GG,¹³⁰ agarose,^{7a} SF¹³¹ and fibrin.^{27c, 132} Hydrogels have recently emerged as a promising platform for 3D cell encapsulation and culture.^{123a} Thus, their biomedical application depends to a large extent on their bulk structure. By controlling the chemical composition and crosslinking density, network structure, and pore size can be tuned and customized for a given application in TE.^{123c} There are several forms to categorize

hydrogels, based on the preparation method, ionic charge or physicochemical structural features. Some of the most used fabrication techniques reported in the last years are highlighted in this section.

(1) *Injectable hydrogels*¹³³ have the potential to be minimally invasive delivered. Most of the hydrogels are injectable, and they can be formed via photopolymerization,^{129, 134} which can be carried out under mild conditions in the presence of living cells. This allows homogeneous seeding of cells throughout the scaffold materials and formation of hydrogels *in situ*.¹²² Alternative polymerization methods include the thermal polymerization,^{133a, 135} by using alginate modified with glycidyl methacrylate and calcium as cross-linker to produce a thermal polymerizable alginate at physiological conditions. Human umbilical vein endothelial cells (HUVECs) were encapsulated in the modified hydrogels *in situ* at 37 °C, revealing that cell viability and proliferation were unaffected by macromonomer concentrations, suggesting the potential application in the field of TE.¹³⁵ However, the lower mechanical properties of the developed hydrogels restrict the potential range of some TE applications. Hybrid injectable hydrogels show to be more complex systems that combine well-evolved biological mechanisms, such as high affinity and specificity of binding, with tailorable hydrogel properties (e.g., mechanical stability and environmental-responsive properties).¹²² Research groups report the development of bioactive organic-inorganic hybrid materials as injectable hydrogel collagen, collagen-chitosan systems for bone tissue regeneration with silica nanoparticles (SiNP) prepared *in situ*.^{133b} The *in vitro* studies on fibroblast cell viability indicated that the SiNP dispersed in the biopolymer matrix had a positive effect on cell viability. Recently, other study reports biohybrid temperature-responsive poly(N-isopropylacrylamide) PNIPAAm-Gelatin-based injectable hydrogel with good bioactivity as well as appropriated mechanical properties for cardiac TE.¹³⁶

(2) *Bioprinting* comprises a group of biofabrication technologies for 3D constructs by precisely printing biocompatible materials, cells and biochemicals in predesigned spatial positions.¹³⁷ During the last years, a more interesting view is the printing and patterning in 3D of all the components that make up a tissue (cells and matrix materials) as a bioink to generate structures analogous to tissue. It can be found different printing approaches based on inject-based and extrusion-based systems that use a nozzle for the deposition of the hydrogel material.¹³⁷⁻¹³⁸

This implies that rheological properties, such as viscosity, shear forces and the mechanism by which the hydrogel is cross-linked to form a stable matrix, plays an important role allowing the ability of the hydrogel to be handled, deposit, stacked and retain volume over the time. Nevertheless, laser-based printers such as stereolithography, are nozzle-free systems that require different properties for the transfer of a hydrogel material from the laser absorbing donor slide to the recipient slide.^{137, 139} These technologies have been successfully applied to fabricate biodegradable 3D constructs with complex architectures and heterogeneous composition. As shown in Figure 6, the use of bioprinting strongly depends on the development of novel biomaterials exhibiting fast crosslinking schemes and appropriate printability, cell-compatibility, degradability and biomechanical properties.^{137, 140}

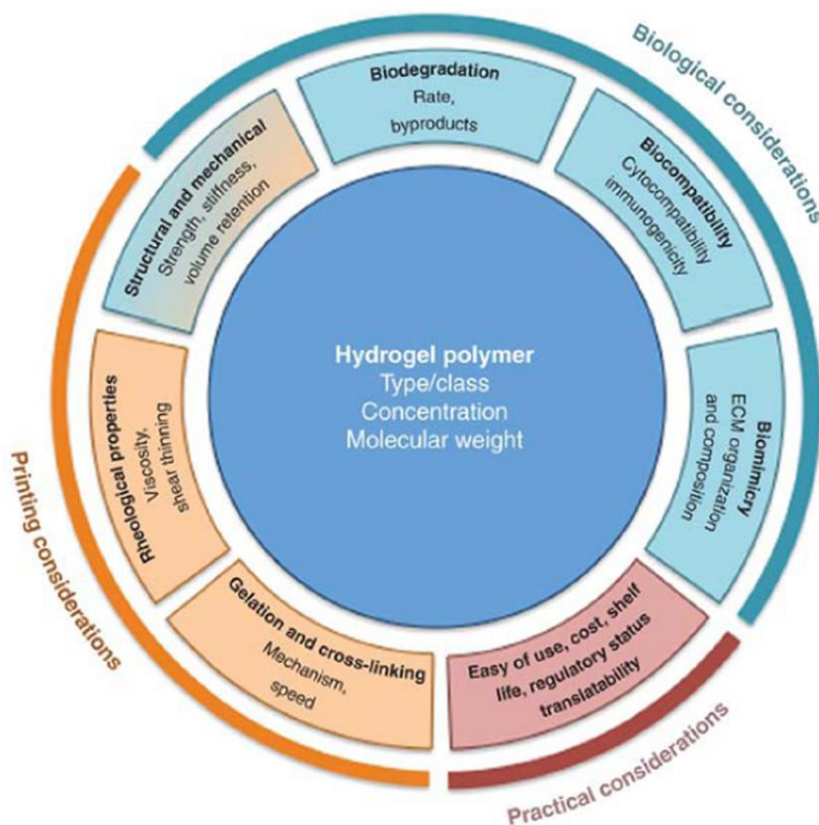


Figure 6: Concept map of the variables and relations to be considered when assessing a hydrogel for bioprinting applications. *Reprinted from Ref¹³⁷ with permission.*

Thus, photocrosslinkable hydrogels showed to be attractive materials for bioprinting since they provide fast polymerization under cell-compatible conditions and excellent spatiotemporal control over the gelation process.^{139a} Since bioprinting uses a layer-by-

layer additive manufacturing approach is of high relevance that the hydrogel presents high viscosity and a fast cross-linking for the fabrication of 3D structures.

Also, after cells been deposit, the hydrogel composition may play an important role in supporting cell viability and proliferation. Figure 7, summarizes the typical process for bioprinting 3D tissues. Very few materials are available that fulfill requirements for bioprinting as well as provide adequate properties for cell encapsulation during and after the printing process. Typical natural materials previously referred in this section included in the hydrogels formulations are alginate and gelatin precursors.^{139a, 141} In a recent study, these precursors were tuned with different concentrations of HAp. *In vitro* studies revealed that hMSCs mixed into the hydrogel precursor survived the printing process and showed high cell viability.¹⁴¹ By adding factors other than HAp, these hydrogels could be used as a bioink for applications in microsphere deposition, drug release and TE applications.

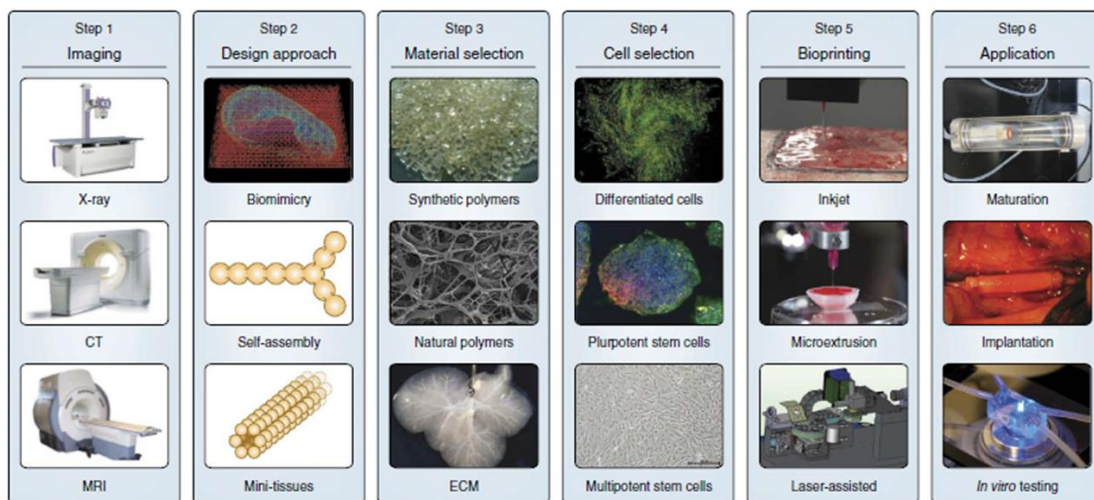


Figure 7: Typical process for bioprinting 3D tissues. Imaging of the damaged tissue and its environment can be used to guide the design of bioprinted tissues. Biomimicry, tissue self-assembly, and mini-tissue building blocks are design approaches used singly and in combination. The choice of materials and cell source is essential and specific to the tissue form and function. Common materials included synthetic or natural polymers and decellularized ECM. Cell sources may be allogeneic or autologous. These components have to integrate with bioprinting systems such as inkjet, microextrusion or laser-assisted printers. Some tissues may require a period of maturation in a bioreactor before transplantation. Alternatively, the 3D tissue may be used for *in vitro* applications. Reprinted from Ref¹⁴² with permission.

(3) *Photolithography* and soft lithography techniques are used for cell encapsulation.¹⁴³ Both methods have also been developed by using a variety of other polymeric biomaterials such as polyethylene glycol (PEG), and alginate hydrogels.¹⁴⁴ Photolithography involves UV light through a photomask on to a substrate coated with a photoresist while; soft lithography includes a range of methods mostly in the field of microfluidics that is used to prepare microstructured elements from a polymeric material.¹⁴⁵ Soft lithography techniques include microfluidic patterning, stencil-assisted patterning, and micro-contact printing. Photolithography can provide a broad range of features, varying from micrometers to sub-microns (*e.g.* 100 nanometres). Photolithography technique uses light or photons to transfer the geometric shapes of a mask to a light-sensitive surface. This fabrication enables to polymerize and cross-link polymers, resulting in a 3D scaffold. Advantages of this technique are the uniform cell encapsulation, the good spatial and temporal control of reaction kinetics, easy control of pore size by varying the selected polymer and its concentration. The main disadvantage is the use of multiple photomasks for multilayered scaffolds and the use of photo-cross-linkable polymers in the photolithography techniques. In addition, some challenges need to be solved such as the lack of resolution, economic viability and unsuitability of UV-sensitive biological materials for patterning.¹⁴⁶ Recent advances show the capability for producing environmentally triggered, self-folding, non-fouling and permeable hydrogel scaffolds, combined with nano- and micropatterned on both surfaces in a one-step photolithographic system.^{143a} This was possible by combining serial hot embossing of sacrificial layers and photolithography. For each pattern, a mastering process was required in which quartz, silicon or PDMS stamps can be prepared, to be used in subsequent hot embossing and photolithography steps. The obtained patterned hydrogel films can be triggered consecutively allowing for successive rolling and unrolling depending on the aqueous pH. Hydrogel photolithography was also developing for integrating cells and sensing elements on culture surfaces (*e.g.* arrays of microwells for single cell capture and entrapment of enzymes inside hydrogel microstructures for local detection of cell metabolism). In both cases, PEG hydrogel lithography can be employed to control cell attachment, in the second approach hydrogel structures also carried enzymes and functioned as cell/sensors interfaces for diagnostics and tissue engineering.¹⁴⁷ Some of these approaches showed promising results not only by biomimetic structures with micropattern nanostructures but also a suitable biochemical

environment. However they are in early stages, and more developments and understanding should be applied to create robust clinical applications.

(4) *Microfluidics* technique deals with the handling of fluids in microenvironments, such as microchannels where the flow of fluids is laminar.^{143c} Microfluidic patterning uses transient microchannels to flow coating agents over restricted areas of a surface.¹⁴⁵ Once the coating is complete, the micro-channels are disassembled, and the patterned surface can be used. Microfluidics has shown advantages for the synthesis of polymer particles and been used to produce hydrogel particles with a well-defined size, shape and morphology.^{145, 148} Most importantly, during the encapsulation process, microfluidics can control the number of cells per particle and the overall encapsulation efficiency.¹⁴⁸ Using this microfabrication technique, it can be found the use of alginate and gelatin as substrates,¹⁴⁹ PEG¹⁵⁰ and typically made of PDMS.^{150b, 151} Important advances have occurred on microfluidic bioassays, which incorporate hydrogel scaffolds into surface-accessible microchambers, driven by the strong demand for the application of spatiotemporally defined biochemical stimuli to construct *in vivo*-like conditions and perform real-time imaging of cell-matrix interactions.¹⁵² One emerging use of microfluidic systems is the generation of shape-controlled hydrogels (i.e., microfibers, microparticles, and hydrogel building blocks) for various biological applications.¹⁵³ The diameters of the hollow and solid fibers can be manipulated by the flow rates.^{153b} Furthermore, the microfluidic fabrication of cell-laden hydrogels is of great benefit for creating artificial scaffolds and should mimic the *in vivo* cellular environment.¹⁵⁴ Temperature-sensitive hydrogels obtained from natural materials (i.e., agarose, gelatin, collagen, and fibrin) have also been used to generate the microfluidic-based tissue architectures.

5. Biomedical/Biotechnological applications

5.1. *Cell encapsulation*

TE construct comprises cells, GFs, and scaffolds. In a traditional TE strategy, cells are seeded on the surface of a porous 3D substrate with appropriate geometry and mechanical properties. In this scenario, cell-cell and cell-matrix interactions occur mainly in 2D. However, on *in vivo* conditions, these interactions happen in a 3D environment, with cells being embedded by the ECM. Bearing this in mind, researchers have been started to

encapsulate viable and functional cells into 3D environments that mimic the natural ECM.¹⁵⁵ Several methods have been used to encapsulate cells in 3D structures, from simple gravitational dripping to more complex ones as microtechnologies¹⁵⁶ or additive manufacturing.¹⁵⁷ This strategy has been shown interesting and promising results for different applications such as, (i) cell immunoisolation and drug delivery;¹⁵⁸ (ii) storage and transport;¹⁵⁹ and (iii) cell delivery.¹⁶⁰ (Figure 8)

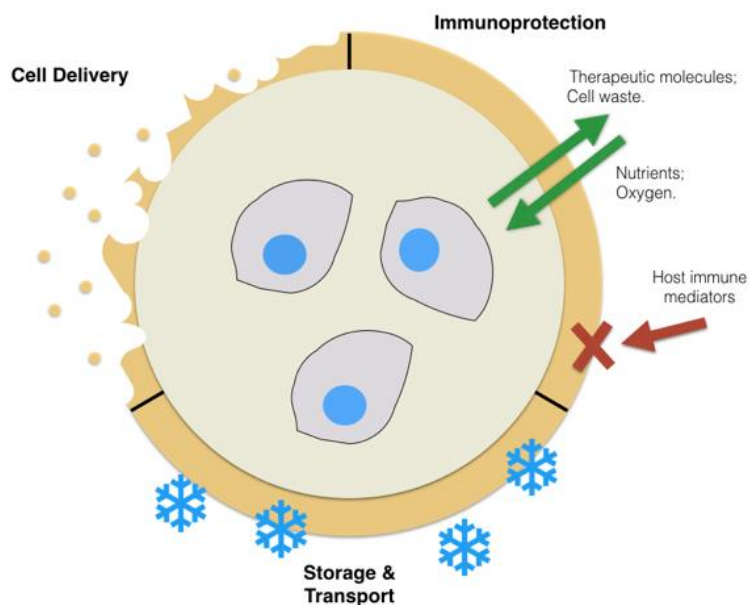


Figure 8: Schematic representation of the three applications of cell encapsulation technology: Cell delivery, Immunoprotection, and Storage&Transport.

Understandably, it is necessary to choose wisely the biomaterial. It should be biocompatible and must be permeable to oxygen, nutrients and metabolites. Naturally-derived hydrogels are attractive materials, as they have a similar structure to the ECM and can be processed under mild conditions, compatible with cells. Moreover, the low interfacial tension between the hydrogels and the environmental fluids results in low protein adsorption rate and cell adhesion, making them highly biocompatible. The soft and pliable nature of these gels reduce the mechanical irritation on the surrounding area, providing a high degree of permeability to nutrients and metabolites.¹⁶¹

Besides biocompatibility and porosity, encapsulation strategies may require other properties that are constrained by the final application of the construct. If the system is

designed for cell delivery, then the matrix should be biodegradable. On the other hand, if the final aim is the release of a therapeutic molecule secreted by entrapped cells, the matrix must be robust and non-biodegradable.

5.1.1. Immunoisolation and drug delivery

Cell encapsulation has been widely studied as a way to avoid the host immune response elicited by transplanted cells. The strategy implies the encapsulation of cells within an artificial compartment, confined by a semipermeable membrane. This membrane must isolate cells from the immune system response – immunoisolation - while permitting the diffusion of small molecules like glucose, oxygen, therapeutic molecules and waste products.¹⁶² As a result, there is no need to use harmful immunosuppressant drugs after transplantation. Moreover, encapsulation technology also surpasses the shortage of donors as it allows not only allogenic but also xenogenic transplants to be performed.¹⁶³ When designing materials for this purpose one should bear in mind some properties that cannot be discarded. First, biomaterials should be selected to prevent cellular overgrowth on the encapsulated grafts while ensuring the free diffusion of nutrients, oxygen, and therapeutic molecules. Otherwise, the overgrowth of fibrous tissue would result in impaired diffusion profiles and subsequent cell death and graft failure. Secondly, they must be stable because the membrane cannot be disrupted after transplantation. Therefore, biodegradable materials with fast degradation kinetics should be avoided for the sake of capsule integrity and subsequent islet immunoprotection.¹⁶⁴ Moreover, materials should have an adequate mechanical stiffness and toughness to handle the forces imposed at the implantation site without disruption.¹⁶² To improve those mechanical properties different geometries and chemical structures are being studied. These include the modification of the material with strengthening polymers, application of multiple layers,¹⁶⁵ reinforcement with polyester meshes and decrease of the capsule size.¹⁶⁴ Last, permeability is a central requirement in the design of cell encapsulation devices, which is tightly correlated with the performance of encapsulated. One important parameter to evaluate membrane permeability is the molecular weight cut-off (MWCO). It determines the minimum molecular weight measured in Daltons (Da), correspondingly minimum size, of a solute that is completely excluded by the semipermeable membrane. A MWCO of 50 to 150 kDa was reported as the most suitable for cell encapsulation purposes.^{162, 164} Immunoisolation techniques have been studied as a treatment for different diseases, including heart infarction,¹⁶⁶ kidney and liver failure,¹⁶⁷ central nervous system

insufficiencies¹⁶⁸ and widely for Diabetes Mellitus.^{165, 169} Inspired by the work of Lim and Sun (1980),¹⁷⁰ islet immunoisolation studies started to consider hydrogels to produce spherical semipermeable membranes (capsules), that host only one to a few islets. Their small size, usually less than 1 mm, and spherical shape enhances the diffusion of oxygen and nutrients across the membrane, promoting cell viability and function.¹⁶⁴ Other advantages of microcapsules include the mechanical stability *in vivo*, ease of manufacturing through different techniques and easy implantation by a simple injection.^{169a} Among the various materials, alginate is the most studied for islet cell microencapsulation, although other materials as silk were also tested.¹⁷¹ Similarly to Lim and Sun, other authors reported the successful application of alginate - poly-L-lysine - alginate microcapsules, using different diabetic models like a rodent, pig, and canine.¹⁷² Human clinical trials were also performed with promising results.^{169b, 172} though, researchers are still facing some complications, mostly regarding the lack of direct vasculature and the fibrotic overgrowth that occurs around the capsules. The lack of direct vasculature associated with encapsulated cells increases the probability of hypoxia, especially at the core of the device, then compromising the cell survival. Fibrotic overgrowth is normally a result of insufficient biocompatibility and has a negative impact on encapsulated islet function, which can lead to islet cell death.¹⁷³ To tackle this issue, Vegas *et al.*¹⁷⁴ used a modified alginate - triazole-thiomorpholine dioxide (TMTD) alginate – as a matrix to encapsulate human stem cell-derived β -cells (SC- β cells). While non-encapsulated SC- β cells were unable to restore a normoglycemic condition, TMTD alginate spheres have provided glycemic correction for over 70 days at all doses tested. Additionally, human C-peptide concentrations were higher when TMTD alginate was used. The immune response to these spheres was also quantified, and the results showed that TMTD alginate spheres had a lower number of cells related to an immune response to their surroundings as compared with other conditions, confirming a reduction in the fibrotic deposition. Further experiments as proteomics and histological processing have confirmed that the TMTD-based material was able to mitigate the fibrotic overgrowth while maintaining islets viable and functional. At last, long-term glycemic control was tested. For that, the created system was transplanted into mice and tracked for 174 days. The mice maintained the glycemic correction for the whole experimental period, with glucose levels similar to the wild-type, even when subjected to a glucose challenge. After six months, the capsules were retrieved, and no fibrotic overgrowth was noticed.

5.1.2 Storage and Transport

Cell-based therapies have grown substantially in recent years as a treatment for numerous diseases including cardiovascular disease, neurodegenerative diseases, cancer, liver disease, diabetes, skeletal disorders and eye diseases.¹⁷⁵ The pipeline from cell isolation to clinical practice implies a storage and transport step, meaning that cell preservation technology must evolve at the same pace to allow correct transport and storage.

The entrapment of living cells within a 3D matrix has been reported as a way to improve cells viability after storage, both on cryo- and hypothermic preservation.^{159, 176} The presence of the biomaterial not only protects cells against the osmotic shock and mechanical stress, experienced during storage and recovery, but also provides cell membrane stabilization and supports the maintenance of cell-cell interactions.¹⁷⁶⁻¹⁷⁷ Consequently, many researchers start to use and study encapsulation methods to store cells. For instance, alginate encapsulation has been investigated for its protective effect on the storage of rat hepatocytes,¹⁷⁷ recombinant baby hamster kidney cells,¹⁷⁸ hBMSCs, mouse embryonic stem cells (ESCs),¹⁷⁹ corneal epithelial cells¹⁸⁰ and adipose stem cells.¹⁵⁹

5.1.2. Cell delivery

The encapsulation of cells inside 3D environments has also been shown promising results for tissue regeneration purposes, where the aim is to form tissue *in vivo* from a TE construct. Besides the aforementioned 3D structure, the encapsulation technique can simplify the handling process and allow a correct grafting of cells. Contrary to immunoisolation, in these cases the material should be biodegradable, allowing cell proliferation and ECM formation to restore the damaged organ. To be successful, the degradation rate should be adjusted to the tissue growth kinetics. Moreover, the degradation products must be cell-friendly to avoid adverse effects on encapsulated cells or in the host.¹⁸¹

Researchers are using different materials and strategies to encapsulate and deliver cells. Fibrous protein-based hydrogels, like silk, keratin, elastin, and collagen have been shown very promising on this topic.¹⁸² Besides the structural, chemical and mechanical similarities with the ECM, they can be degraded by proteolytic enzymes once inside the human body.¹⁸² Carbohydrate-based materials, including mixtures¹⁸³ or chemically modified¹⁸⁴ materials, as well as hydrogel composites,^{123c} are also very promising since

the modifications can improve and help on fine tune their degradation rate,^{183b, 185} according to with the desired purpose.

One interesting approach for cell delivery is the use of injectable cell-laden hydrogels.^{184, 186} This strategy has called the attention of researchers mostly due to its non-invasive nature as well as the ease of handling and possibility to completely fill the defect. Recently, Liu *et al.*^{186a} developed a thermosensitive carboxymethyl chitin hydrogel that sets at 37 °C and it is degraded in the presence of lysozyme or hyaluronidase. These hydrogels were able to promote cell proliferation and survival *in vitro* and *in vivo* studies showed tissue compatibility and good *in-situ* gel formation.

5.2. Application in Intervertebral Disc Regeneration

Several polymers have been studied for intervertebral disc (IVD) regeneration, namely natural-origin polymers that can be used as hydrogel matrices or 3D porous scaffolds.¹⁸⁷ Despite the great advances using cell-free materials and growth factors, the use of acellular strategies combined with cells obtained from different sources is seen as the most promising research direction. Cell-based strategies directed to the regeneration of IVD focus mainly on the regeneration of the central nucleus (nucleus pulposus, NP), since it is in this tissue that disc degeneration initiates. The outer structure of the IVD, i.e. the annulus fibrosus (AF), suffers degeneration after the NP, mainly due to NP malfunction because of its loss of hydration and structure.¹⁸⁸ So when choosing the right biomaterial to carry cells to the NP, several properties must be taken into account, namely (Table 2):

Table 2. Biomaterial requirements as a cell carrier for IVD regeneration.

	Problem	Solution	References
1	AF should be left intact as much as possible during surgical procedure	Injectable material, so that only the area of the needle insertion in the AF is injured	189
2	The material must be able to polymerise <i>in situ</i> only after injection *	Polymerization can be achieved either by changes in pH, ion interaction, temperature or light exposure	190,191
3	The cell-loaded material should improve NP properties, such as disc height and biomechanical	The material's mechanical properties should be as close as possible to the mechanical properties of the native NP tissue	192

	function, for the cells to remain viable		
4	The biomaterial must provide an adequate environment for stimulation of NP cells phenotype	The material must be able to absorb at least 80% of water, which is the amount of water in the NP	193
5	The material should be biocompatible and biodegradable	The degradability rate must have the same timing has the tissue's rate of regeneration	194

*If the polymerised material can be injected or if the material does not polymerise *in vivo* it is very likely that the material will come right off through the needle hole, with cells included, on the first IVD loading.

With all those requirements in mind, hydrogels stand out as the best type of material to be used for NP regeneration (Figure 9). Hydrogels can withstand complex loading and allow the complete filling of irregular defects.¹⁸⁷ In the clinical setting, they possibly to be administered by using minimally invasive techniques, facilitating a good and faster surgical practice. Additionally, hydrogels present less risk of extrusion or migration, thus allowing to control the delivery of drugs or cells at the damaged site. Hydrogels for IVD repair may differ from physical crosslinking systems (e.g. ionic-crosslinked), which are obtained under mild conditions, to chemical crosslinking systems (e.g. photo- and enzyme-crosslinked) that present improved stability and mechanical properties.

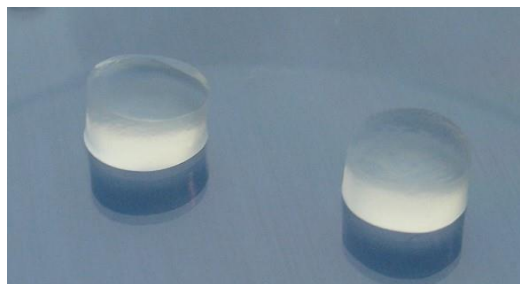


Figure 9: Ionically-crosslinked methacrylated GG (GG-MA) discs with a diameter of 7 mm and a height of 4 mm.

Several kinds of hydrogels have been studied for cartilage regeneration, as well as specifically designed for IVD TE strategies. There is a growing interest in natural-origin hydrogels, and besides their high biocompatibility, the economic aspect is another reason for it. The main reasons for why they are getting more attractive are their low toxicity and the wide range of possible TE strategies where they can be applied.¹⁹⁵ Additionally, as most of the naturally occurring hydrogels are extracted and not synthesized, this greatly

reduces its manufacturing cost. However, they also require purification processing, which sometimes involves using severely toxic solvents and reagents. Even so, in general, they are less expensive to produce than synthetic hydrogels.

Although natural-origin hydrogels offer a wide range of biological advantages, they lack the needed physical properties, such as solubility and adequate rate of degradation, which is too fast and does not allow the tissue to regenerate in such low time.¹⁹⁶ Some examples of natural-origin hydrogels being investigated for IVD TE are alginate, carboxymethylcellulose, chitosan, collagen, gellan gum, hyaluronan and silk fibroin.^{48, 130b, 192, 195a, 195c, 197} The advantages and disadvantages of using each one of these natural-origin polymers in NP regeneration are indicated in Table 3.

Table 3. Natural-origin hydrogels used in IVD TE strategies – advantages and disadvantages specific for NP regeneration.

Natural Origin Hydrogels	Advantages	Disadvantages	References
Alginate	<ul style="list-style-type: none"> - Polymerization under mild conditions - <i>In situ</i> injectability - closely mimics NP mechanical and cell-adhesive properties 	<ul style="list-style-type: none"> - Limited control over mechanical properties, swelling ratio and degradation profile - High variability between batches due to impurities presence - Immunogenic - Difficult to sterilize and handle - Lack of informational structure for positive cell response 	197a,195c, 197b,197c,197d
Carboxymethyl cellulose	<ul style="list-style-type: none"> - Low-cost - FDA-approved - Commercially available in high-purity forms 	<ul style="list-style-type: none"> - Lack of studies on IVD regeneration 	197e,197f
Chitosan	<ul style="list-style-type: none"> - Hydrophilic surface - Bioactive - Cell adherent - Antibacterial activity - Non immunogenic 	<ul style="list-style-type: none"> - Poor mechanical properties - Some level of toxicity (due to crosslinking agents) 	197a, 195c, 197g,192

		- High variability between batches due to impurities presence	
Collagen	- Non- immunogenic - Piezoelectric properties - Bioactive	- Poor mechanical properties - High degradation rate - Some level of toxicity (due to crosslinking agents)	197a,195c,197h
Gellan Gum	- Non- immunogenic - Very low manufacturing cost - Stable in long-term - Mechanical performance and rheological behavior similar to the native NP tissue - Non-angiogenic when methacrylated	- Weak in physiological conditions in its native form due to the exchange of divalent cations by monovalent ones	48, 197a, 197i,130b, 197j
Hyaluronan	- Non-immunogenic - Easy control over polymer chain sizes - Bioactive	- Osteogenic - Cytotoxic in high concentration - Batch-to-batch variations	197a, 195c,197k, 197l
Silk Fibroin	- Good mechanical properties - Biocompatible - Controllable degradation rate - Can provide appropriate mechanical strength when combined with other polymers	- Can only be used to create composite hydrogels due to inducible formation of crystalline b-sheet structure	197m, 197n

6. Final remarks and future trends

Natural-origin polymers derived from renewable resources, namely from algae, animal, plant, and microorganisms, are appealing for tissue engineering and regenerative medicine applications due to its similarities with the extracellular matrix, specific degradation rates, chemical versatility, and good biological performance without toxicity or immunological reactions. A variety of applications for these type of materials includes cell encapsulation and intervertebral disc (IVD) regeneration. Biomimetic strategies for tissue engineering and processing are focused on micro/nanoparticles, membranes, scaffolds, and hydrogels, alone or in combination. Hydrogels are of particular interest because of their high water content, biodegradability and compatibility, and mechanical properties which resemble those of nonosseous living tissues. Many efforts have been made to improve the hydrogels potential. Injectable hydrogels, including mixtures of organic-inorganic systems, will continue to be improved and applied in areas for tissue enhancement and regeneration. Moreover, specific microfabrication techniques will be improved to spatially pattern the environment at microscale. One disadvantage of processing hydrogels is difficult to shape them in predesigned geometries. A challenge for tissue engineering is producing 3D vascularized cellular constructs of clinically relevant size, shape and structural integrity.

Conventional techniques used to fabricate structures include foam replica method, solvent casting and particulate-leaching, freeze drying, gas foaming, and phase separation. Rapid prototyping, supercritical fluid technology bioprinting, photolithography, microfluidics, and electrospinning, are more sophisticated techniques also used allowing the possibility of incorporating pharmaceutical agents and possibly cells.

Additive manufacturing such as bioprinting and bioink presents a high potential in combination with the design and imaging techniques. This includes the evolution and understanding of microfluidic devices whose controlled environments provide the cell culture with more life-like conditions than traditional cell culture methods. The innovations of these systems at the micro and nanoscale will open a wide range of applications, from fundamental research up to regenerative medicine.

The use of natural-derived polymers allows to better mimic the native ECM environment. Then, these molecules are very attractive for biomimetic strategies, including cell encapsulation. Nevertheless, their inherent properties are not enough to confer the perfect environment for cell growth and provide the proper mechanical properties. As a result,

they are commonly combined with other materials, both natural or synthetic, to obtain improved TE constructs. Thence, the development of new strategies or their translation to clinics are tightly dependent on the development and study of new biomaterials or combinations of well-established ones.

ACKNOWLEDGEMENTS: The authors would like to thank to the financial support from the Portuguese Foundation for Science and Technology (FCT) for the fellowship grants of Simone S Silva (SFRH/BPD/112140/2015), Emanuel M Fernandes (SFRH/BPD/96197/2013), Joana-Silva Correia (SFRH/BPD/100590/2014), Sandra Pina (SFRH/BPD/108763/2015), Silvia Vieira (SFRH/BD/102710/2014), “Fundo Social Europeu”- FSE and “ Programa Diferencial de Potencial Humano POPH”, and to the distinction attributed to J.M. Oliveira under the Investigator FCT program (IF/00423/2012). It is also greatly acknowledged the funds provided by FCT through the project EPIDisc (UTAP-EXPL/BBBECT/0050/2014), financed in the Framework of the “International Collaboratory for Emerging Technologies, CoLab”, UT Austin|Portugal Program.

References

1. (a) Silva, S. S.; Mano, J. F.; Reis, R. L., Potential applications of natural origin polymer-based systems in soft tissue regeneration. *Critical Reviews in Biotechnology* **2010**, *30* (3), 200-221; (b) Mano, J. F.; Silva, G. A.; Azevedo, H. S.; Malafaya, P. B.; Sousa, R. A.; Silva, S. S.; Boesel, L. F.; Oliveira, J. M.; Santos, T. C.; Marques, A. P.; Neves, N. M.; Reis, R. L., Natural origin biodegradable systems in tissue engineering and regenerative medicine: present status and some moving trends. *Journal of the Royal Society Interface* **2007**, *4* (17), 999-1030.
2. (a) Liu, J.; Willför, S.; Xu, C., A review of bioactive plant polysaccharides: Biological activities, functionalization, and biomedical applications. *Bioactive Carbohydrates and Dietary Fibre* **2015**, *5* (1), 31-61; (b) Khan, F.; Ahmad, S. R., Polysaccharides and Their Derivatives for Versatile Tissue Engineering Application. *Macromolecular Bioscience* **2013**, *13* (4), 395-421; (c) D' Ayala, G.; Malinconico, M.; Laurienzo, P., Marine Derived Polysaccharides for Biomedical Applications: Chemical Modification Approaches. *Molecules* **2008**, *13* (9), 2069.
3. Lee, K. Y.; Mooney, D. J., Alginate: Properties and biomedical applications. *Progress in Polymer Science* **2012**, *37* (1), 106-126.
4. Hernández-Carmona, G.; McHugh, D. J.; Arvizu-Higuera, D. L.; Rodríguez-Montesinos, Y. E., Pilot plant scale extraction of alginates from *Macrocystis pyrifera* 4. Conversion of alginic acid to sodium alginate, drying and milling. *Journal of Applied Phycology* **2002**, *14* (6), 445-451.
5. Yang, J.; Han, S.; Zheng, H.; Dong, H.; Liu, J., Preparation and application of micro/nanoparticles based on natural polysaccharides. *Carbohydrate Polymers* **2015**, *123*, 53-66.
6. Fernández, E.; López, D.; Mijangos, C.; Duskova-Smrckova, M.; Ilavsky, M.; Dusek, K., Rheological and thermal properties of agarose aqueous solutions and hydrogels. *Journal of Polymer Science Part B: Polymer Physics* **2008**, *46* (3), 322-328.
7. (a) Miguel, S. P.; Ribeiro, M. P.; Brancal, H.; Coutinho, P.; Correia, I. J., Thermoresponsive chitosan-agarose hydrogel for skin regeneration. *Carbohydr Polym* **2014**, *111*, 366-73; (b) Carriel, V.; Garzón, I.; Jiménez, J. M.; Oliveira, A. C. X.; Arias-Santiago, S.; Campos, A.; Sánchez-Quevedo, M. C.; Alaminos, M., Epithelial and Stromal Developmental Patterns in a Novel Substitute of the Human Skin Generated with Fibrin-Agarose Biomaterials. *Cells Tissues Organs* **2012**, *196* (1), 1-12.
8. Carriel, V.; Garrido-Gomez, J.; Hernandez-Cortes, P.; Garzon, I.; Garcia-Garcia, S.; Saez-Moreno, J. A.; Sanchez-Quevedo, M. D. C.; Campos, A.; Alaminos, M., Combination of fibrin-agarose hydrogels and adipose-derived mesenchymal stem cells for peripheral nerve regeneration. *J Neural Eng* **2013**, *10* (2).
9. (a) Liu, J.; Zhan, X.; Wan, J.; Wang, Y.; Wang, C., Review for carrageenan-based pharmaceutical biomaterials: favourable physical features versus adverse biological effects. *Carbohydr Polym* **2015**, *121*, 27-36; (b) Popa, E. G.; Carvalho, P. P.; Dias, A. F.; Santos, T. C.; Santo, V. E.; Marques, A. P.; Viegas, C. A.; Dias, I. R.; Gomes, M. E.; Reis, R. L., Evaluation of the in vitro and in vivo biocompatibility of carrageenan-based hydrogels. *Journal of biomedical materials research. Part A* **2014**, *102* (11), 4087-97; (c) Mihaila, S. M.; Gaharwar, A. K.; Reis, R. L.; Marques, A. P.; Gomes, M. E.; Khademhosseini, A., Photocrosslinkable kappa-carrageenan hydrogels for tissue engineering applications. *Advanced healthcare materials* **2013**, *2* (6), 895-907.
10. Ale, M. T.; Mikkelsen, J. D.; Meyer, A. S., Important Determinants for Fucoidan Bioactivity: A Critical Review of Structure-Function Relations and Extraction Methods

for Fucose-Containing Sulfated Polysaccharides from Brown Seaweeds. *Marine Drugs* **2011**, *9* (10), 2106-2130.

11. (a) Fitton, J. H.; Stringer, D.; Karpinić, S., Therapies from Fucoidan: An Update. *Mar. Drugs* **2015**, *13*(9), ; **2015**, *13* (9), 5920-5946; (b) Purnama, A.; Aid-Launais, R.; Haddad, O.; Maire, M.; Mantovani, D.; Letourneur, D.; Hlawaty, H.; Le Visage, C., Fucoidan in a 3D scaffold interacts with vascular endothelial growth factor and promotes neovascularization in mice. *Drug delivery and translational research* **2015**, *5* (2), 187-97.

12. Alves, A.; Sousa, R. A.; Reis, R. L., A practical perspective on ulvan extracted from green algae. *Journal of Applied Phycology* **2013**, *25* (2), 407-424.

13. Morelli, A.; Betti, M.; Puppi, D.; Bartoli, C.; Gazzarri, M.; Chiellini, F., Enzymatically Crosslinked Ulvan Hydrogels as Injectable Systems for Cell Delivery. *Macromol Chem Phys* **2016**, *217* (4), 581-590.

14. Dash, M.; Samal, S. K.; Bartoli, C.; Morelli, A.; Smet, P. F.; Dubruel, P.; Chiellini, F., Biofunctionalization of Ulvan Scaffolds for Bone Tissue Engineering. *ACS Appl. Mater. Interfaces* **2014**, *6* (5), 3211-3218.

15. (a) Cheung, R. C. F.; Ng, T. B.; Wong, J. H.; Chan, W. Y., Chitosan: An Update on Potential Biomedical and Pharmaceutical Applications. *Marine Drugs* **2015**, *13* (8), 5156-5186; (b) Silva, S. S.; Popa, E. G.; Gomes, M. E.; Cerqueira, M.; Marques, A. P.; Caridade, S. G.; Teixeira, P.; Sousa, C.; Mano, J. F.; Reis, R. L., An investigation of the potential application of chitosan/aloe-based membranes for regenerative medicine. *Acta biomaterialia* **2013**, *9* (6), 6790-6797.

16. Silva, T. H.; Alves, A.; Ferreira, B. M.; Oliveira, J. M.; Reys, L. L.; Ferreira, R. J. F.; Sousa, R. A.; Silva, S. S.; Mano, J. F.; Reis, R. L., Materials of marine origin: a review on polymers and ceramics of biomedical interest. *International Materials Reviews* **2012**, *57* (5), 276-306.

17. Anthony, J.; Brennecke, J.; Holbrey, J.; Maginn, E.; Mantz, P.; Trulove, A. V.; Welton, T., Physicochemical Properties of Ionic Liquids In *Ionic Liquids in Synthesis*, Wasserscheid, P.; Welton, T., Eds. Wiley-VCH, 2002; pp 41-126.

18. (a) Silva, S. S.; Duarte, A. R.; Carvalho, A. P.; Mano, J. F.; Reis, R. L., Green processing of porous chitin structures for biomedical applications combining ionic liquids and supercritical fluid technology. *Acta biomaterialia* **2011**, *7* (3), 1166-72; (b) Silva, S. S.; Duarte, A. R. C.; Mano, J. F.; Reis, R. L., Design and functionalization of chitin-based microsphere scaffolds. *Green Chemistry* **2013**, *15* (11), 3252-3258; (c) Silva, S. S.; Duarte, A. R. C.; Oliveira, J. M.; Mano, J. F.; Reis, R. L., Alternative methodology for chitin-hydroxyapatite composites using ionic liquids and supercritical fluid technology. *Journal of Bioactive and Compatible Polymers* **2013**, *28* (5), 481-491.

19. Silva, S. S.; Santos, T. C.; Cerqueira, M. T.; Marques, A. P.; Reys, L. L.; Silva, T. H.; Caridade, S. G.; Mano, J. F.; Reis, R. L., The use of ionic liquids in the processing of chitosan/silk hydrogels for biomedical applications. *Green Chemistry* **2012**, *14* (5), 1463-1470.

20. Isik, M.; Sardon, H.; Mecerreyes, D., Ionic Liquids and Cellulose: Dissolution, Chemical Modification and Preparation of New Cellulosic Materials. *International Journal of Molecular Sciences* **2014**, *15* (7), 11922-11940.

21. (a) Silva, S.; Popa, E. G.; Gomes, M. E.; Oliveira, M. B.; Nayak, S.; Subia, B.; Mano, J. F.; Kundu, S.; Reis, R. L., Silk hydrogels from non-mulberry and mulberry silkworm cocoons processed with ionic liquids. *Acta biomaterialia* **2013**, *S1742-7061(13)00337-1*; (b) Silva, S. S.; Oliveira, N. M.; Oliveira, M. B.; da Costa, D. P. S.; Naskar, D.; Mano, J. F.; Kundu, S. C.; Reis, R. L., Fabrication and characterization of Eri

silk fibers-based sponges for biomedical application. *Acta biomaterialia* **2016**, *32*, 178-189.

22. Abdelaal, O.; Darwish, S., Fabrication of tissue engineering scaffolds using rapid prototyping techniques. *World Academy of Science, Engineering and Technology* **2011**, *59*, 577-85.

23. (a) Ciechanska, D., Multifunctional bacterial cellulose/chitosan composite materials for medical applications. *Fibres Text East Eur* **2004**, *12* (4), 69-72; (b) Ruphuy, G.; Saralegi, A.; Lopes, J. C.; Dias, M. M.; Barreiro, M. F., Spray drying as a viable process to produce nano-hydroxyapatite/chitosan (n-HAp/CS) hybrid microparticles mimicking bone composition. *Advanced Powder Technology* **2016**, *27* (2), 575-583.

24. (a) Esquivel, R.; Juárez, J.; Almada, M.; Ibarra, J.; Valdez, M. A., Synthesis and Characterization of New Thiolated Chitosan Nanoparticles Obtained by Ionic Gelation Method. *International Journal of Polymer Science* **2015**, *2015*; (b) Huang, Y. C.; Yang, Y. T., Effect of basic fibroblast growth factor released from chitosan-fucoidan nanoparticles on neurite extension. *Journal of tissue engineering and regenerative medicine* **2013**.

25. Sugahara, K.; Mikami, T.; Uyama, T.; Mizuguchi, S.; Nomura, K.; Kitagawa, H., Recent advances in the structural biology of chondroitin sulfate and dermatan sulfate. *Current Opinion in Structural Biology* **2003**, *13* (5), 612-620.

26. Highley, C. B.; Prestwich, G. D.; Burdick, J. A., Recent advances in hyaluronic acid hydrogels for biomedical applications. *Current opinion in biotechnology* **2016**, *40*, 35-40.

27. (a) Menegatti, S.; Ruocco, N.; Kumar, S.; Zakrewsky, M.; Sanchez De Oliveira, J.; Helgeson, M. E.; Leal, G. L.; Mitragotri, S., Synthesis and characterization of a self-fluorescent hyaluronic acid-based gel for dermal applications. *Advanced healthcare materials* **2015**, *4* (15), 2297-305; (b) Domingues, R. M. A.; Silva, M.; Gershovich, P.; Betta, S.; Babo, P.; Caridade, S. G.; Mano, J. F.; Motta, A.; Reis, R. L.; Gomes, M. E., Development of Injectable Hyaluronic Acid/Cellulose Nanocrystals Bionanocomposite Hydrogels for Tissue Engineering Applications. *Bioconjugate Chemistry* **2015**, *26* (8), 1571-1581; (c) Kang, S.-W.; Kim, J.-S.; Park, K.-S.; Cha, B.-H.; Shim, J.-H.; Kim, J. Y.; Cho, D.-W.; Rhie, J.-W.; Lee, S.-H., Surface modification with fibrin/hyaluronic acid hydrogel on solid-free form-based scaffolds followed by BMP-2 loading to enhance bone regeneration. *Bone* **2011**, *48* (2), 298-306.

28. Hamman, J., Composition and Applications of Aloe vera Leaf Gel. *Molecules* **2008**, *13* (8), 1599.

29. Sierra-Garcia, G. D.; Castro-Rios, R.; Gonzalez-Horta, A.; Lara-Arias, J.; Chavez-Montes, A., Acemannan, an Extracted Polysaccharide from Aloe vera: A Literature Review. *Nat Prod Commun* **2014**, *9* (8), 1217-1221.

30. (a) Chauhan, A.; Zubair, S.; Sherwani, A.; Owais, M., Aloe vera Induced Biomimetic Assemblage of Nucleobase into Nanosized Particles. *PLoS ONE* **2012**, *7* (3), e32049; (b) Sahu, P.; Giri, D.; Singh, R.; Pandey, P.; Gupta, S.; Shrivastava, A.; Kumar, A.; Pandey, K., Therapeutic and Medicinal Uses of Aloe vera: A Review. *Pharmacology & Pharmacy* **2013**, *4* (8), 599-610.

31. Boonyagul, S.; Banlunara, W.; Sangvanich, P.; Thunyakitpisal, P., Effect of acemannan, an extracted polysaccharide from Aloe vera, on BMSCs proliferation, differentiation, extracellular matrix synthesis, mineralization, and bone formation in a tooth extraction model. *Odontology* **2014**, *102* (2), 310-317.

32. Jettanacheawchankit, S.; Sasithanasate, S.; Sangvanich, P.; Banlunara, W.; Thunyakitpisal, P., Acemannan Stimulates Gingival Fibroblast Proliferation; Expressions

- of Keratinocyte Growth Factor-1, Vascular Endothelial Growth Factor, and Type I Collagen; and Wound Healing. *J Pharmacol Sci* **2009**, *109* (4), 525-531.
33. Jittapiromsak, N.; Sahawat, D.; Banlunara, W.; Sangvanich, P.; Thunyakitpisal, P., Acemannan, an Extracted Product from Aloe Vera, Stimulates Dental Pulp Cell Proliferation, Differentiation, Mineralization, and Dentin Formation. *Tissue Eng Pt A* **2010**, *16* (6), 1997-2006.
34. Chantarawaratit, P.; Sangvanich, P.; Banlunara, W.; Soontornvipart, K.; Thunyakitpisal, P., Acemannan sponges stimulate alveolar bone, cementum and periodontal ligament regeneration in a canine class II furcation defect model. *J Periodontal Res* **2014**, *49* (2), 164-178.
35. Fernandes, E. M.; Pires, R. A.; Mano, J. F.; Reis, R. L., Bionanocomposites from lignocellulosic resources: Properties, applications and future trends for their use in the biomedical field. *Progress in Polymer Science* **2013**, *38* (10–11), 1415-1441.
36. Park, T.-J.; Jung, Y.; Choi, S.-W.; Park, H.; Kim, H.; Kim, E.; Lee, S.; Kim, J., Native chitosan/cellulose composite fibers from an ionic liquid via electrospinning. *Macromol. Res.* **2011**, *19* (3), 213-215.
37. Morrison, W. R.; Karkalas, J., Starch. In *Methods in plant biochemistry. Carbohydrates*, Dey, P., Ed. Academic Press Limited: London, 1990; Vol. 2, pp 323-352.
38. (a) Klemm, D.; Heublein, B.; Fink, H.-P.; Bohn, A., Cellulose: Fascinating Biopolymer and Sustainable Raw Material. *Angewandte Chemie International Edition* **2005**, *44* (22), 3358-3393; (b) Svensson, A.; Nicklasson, E.; Harrah, T.; Panilaitis, B.; Kaplan, D. L.; Brittberg, M.; Gatenholm, P., Bacterial cellulose as a potential scaffold for tissue engineering of cartilage. *Biomaterials* **2005**, *26* (4), 419-431; (c) Brown, R. M.; Czaja, W. K.; Young, D. J.; Kawecki, M., The future prospects of microbial cellulose in biomedical applications. *Biomacromolecules* **2007**, *8* (1), 1-12.
39. Helenius, G.; Backdahl, H.; Bodin, A.; Nannmark, U.; Gatenholm, P.; Risberg, B., In vivo biocompatibility of bacterial cellulose. *Journal of Biomedical Materials Research* **2006**, *76A*, 431-438.
40. Wiegand, C.; Elsner, P.; Hipler, U. C.; Klemm, D., Protease and ROS activities influenced by a composite of bacterial cellulose and collagen type I in vitro. *Cellulose* **2006**, *13* (6), 689-696.
41. Zhang, P.; Chen, L.; Zhang, Q. S.; Hong, F. F., Using In situ Dynamic Cultures to Rapidly Biofabricate Fabric-Reinforced Composites of Chitosan/Bacterial Nanocellulose for Antibacterial Wound Dressings. *Front Microbiol* **2016**, *7*.
42. Godinho, J. F.; Berti, F. V.; Muller, D.; Rambo, C. R.; Porto, L. M., Incorporation of Aloe vera extracts into nanocellulose during biosynthesis. *Cellulose* **2016**, *23* (1), 545-555.
43. Abeer, M. M.; Mohd Amin, M. C. I.; Martin, C., A review of bacterial cellulose-based drug delivery systems: their biochemistry, current approaches and future prospects. *Journal of Pharmacy and Pharmacology* **2014**, *66* (8), 1047-1061.
44. Wu, H.; Wang, H.; Cheng, F.; Xu, F.; Cheng, G., Synthesis and characterization of an enzyme-degradable zwitterionic dextran hydrogel. *RSC Advances* **2016**, *6* (37), 30862-30866.
45. Sun, G. M.; Mao, J. J., Engineering dextran-based scaffolds for drug delivery and tissue repair. *Nanomedicine-Uk* **2012**, *7* (11), 1771-1784.
46. Banerjee, A.; Bandopadhyay, R., Use of dextran nanoparticle: A paradigm shift in bacterial exopolysaccharide based biomedical applications. *International journal of biological macromolecules* **2016**, *87*, 295-301.
47. (a) Oliveira, J. T.; Picciochi, R.; Santos, T. C.; Martins, L.; Pinto, L. G.; Malafaya, P. B.; Sousa, R. A.; Marques, A. P.; Castro, A. G.; Mano, J. F.; Neves, N. M.; Reis, R.

- L., Injectable gellan gum hydrogels as supports for cartilage tissue engineering applications. *Tissue Eng Pt A* **2008**, *14* (5), 748-748; (b) Oliveira, J. T.; Santos, T. C.; Martins, L.; Picciochi, R.; Marques, A. P.; Castro, A. G.; Neves, N. M.; Mano, J. F.; Reis, R. L., Gellan Gum Injectable Hydrogels for Cartilage Tissue Engineering Applications: In Vitro Studies and Preliminary In Vivo Evaluation. *Tissue Eng Pt A* **2010**, *16* (1), 343-353.
48. Silva-Correia, J.; Oliveira, J. M.; Caridade, S. G.; Oliveira, J. T.; Sousa, R. A.; Mano, J. F.; Reis, R. L., Gellan gum-based hydrogels for intervertebral disc tissue-engineering applications. *Journal of tissue engineering and regenerative medicine* **2011**, *5* (6), E97-E107.
49. Ramshaw, J. A., Biomedical applications of collagens. *Journal of biomedical materials research. Part B, Applied biomaterials* **2016**, *104* (4), 665-75.
50. Su, K.; Wang, C. M., Recent advances in the use of gelatin in biomedical research. *Biotechnol Lett* **2015**, *37* (11), 2139-2145.
51. Yue, K.; Trujillo-de Santiago, G.; Alvarez, M. M.; Tamayol, A.; Annabi, N.; Khademhosseini, A., Synthesis, properties, and biomedical applications of gelatin methacryloyl (GelMA) hydrogels. *Biomaterials* **2015**, *73*, 254-71.
52. Almine, J. F.; Bax, D. V.; Mithieux, S. M.; Nivison-Smith, L.; Rnjak, J.; Waterhouse, A.; Wise, S. G.; Weiss, A. S., Elastin-based materials. *Chemical Society Reviews* **2010**, *39* (9), 3371-3379.
53. Costa, R. R.; Martín, L.; Mano, J. F.; Rodríguez-Cabello, J. C., Elastin-Like Macromolecules. In *Biomimetic Approaches for Biomaterials Development*, Wiley-VCH Verlag GmbH & Co. KGaA: 2012; pp 93-116.
54. Gagner, J. E.; Kim, W.; Chaikof, E. L., Designing protein-based biomaterials for medical applications. *Acta biomaterialia* **2014**, *10* (4), 1542-1557.
55. Kundu, S. C.; Kundu, B.; Talukdar, S.; Bano, S.; Nayak, S.; Kundu, J.; Mandal, B. B.; Bhardwaj, N.; Botlagunta, M.; Dash, B. C.; Acharya, C.; Ghosh, A. K., Nonmulberry silk biopolymers. *Biopolymers* **2012**, *97* (6), 455-467.
56. Melke, J.; Midha, S.; Ghosh, S.; Ito, K.; Hofmann, S., Silk fibroin as biomaterial for bone tissue engineering. *Acta biomaterialia* **2016**, *31*, 1-16.
57. Kundu, S. C.; Dash, B. C.; Dash, R.; Kaplan, D. L., Natural protective glue protein, sericin bioengineered by silkworms: Potential for biomedical and biotechnological applications. *Progress in Polymer Science* **2008**, *33* (10), 998-1012.
58. Kundu, B.; Kundu, S. C., Silk sericin/polyacrylamide in situ forming hydrogels for dermal reconstruction. *Biomaterials* **2012**, *33* (30), 7456-7467.
59. Lamboni, L.; Gauthier, M.; Yang, G.; Wang, Q., Silk sericin: A versatile material for tissue engineering and drug delivery. *Biotechnology advances* **2015**, *33* (8), 1855-67.
60. Tansaz, S.; Boccaccini, A. R., Biomedical applications of soy protein: A brief overview. *Journal of biomedical materials research. Part A* **2016**, *104* (2), 553-69.
61. Were, L.; Hettiarachchy, N. S.; Coleman, M., Properties of cysteine-added soy protein-wheat gluten films. *Journal of Food Science* **1999**, *64* (3), 514-518.
62. Vaz, C. M.; Fossen, M.; van Tuil, R. F.; de Graaf, L. A.; Reis, R. L.; Cunha, A. M., Casein and soybean protein-based thermoplastics and composites as alternative biodegradable polymers for biomedical applications. *Journal of Biomedical Materials Research Part A* **2003**, *65A* (1), 60-70.
63. Chen, Y.; Zhang, L. N., Blend membranes prepared from cellulose and soy protein isolate in NaOH/thiourea aqueous solution. *J Appl Polym Sci* **2004**, *94* (2), 748-757.
64. (a) Silva, R. M.; Elvira, c.; Mano, J. F.; Román, J. S.; Reis, R. L., Influence of Beta-Radiation Sterilization in Properties of New Chitosan/Soybean Protein Isolate Membranes for Guided Bone Regeneration *Journal of Materials Science-Materials in*

- Medicine* **2004**, *15*, 523-528; (b) Silva, S. S.; Santos, M. I.; Coutinho, O. P.; Mano, J. F.; Reis, R. L., Physical properties and biocompatibility of chitosan/soy blended membranes. *Journal of Materials Science-Materials in Medicine* **2005**, *16* (6), 575-579.
65. Vaz, C. M.; Graaf, L. A.; Reis, R. L.; Cunha, A. M., *Soy protein-based systems for different tissue regeneration applications*. Kluwer Academic Publishers: 2002; p 93-110.
66. Lee, K.; Silva, E. A.; Mooney, D. J., Growth factor delivery-based tissue engineering: general approaches and a review of recent developments. *Journal of The Royal Society Interface* **2011**, *8* (55), 153-170.
67. Oliveira, S. M.; Santo, V. E.; Gomes, M. E.; Reis, R. L.; Mano, J. F., Layer-by-layer assembled cell instructive nanocoatings containing platelet lysate. *Biomaterials* **2015**, *48*, 56-65.
68. (a) Wang, R. N.; Green, J.; Wang, Z.; Deng, Y.; Qiao, M.; Peabody, M.; Zhang, Q.; Ye, J.; Yan, Z.; Denduluri, S.; Idowu, O.; Li, M.; Shen, C.; Hu, A.; Haydon, R. C.; Kang, R.; Mok, J.; Lee, M. J.; Luu, H. L.; Shi, L. L., Bone Morphogenetic Protein (BMP) signaling in development and human diseases. *Genes & Diseases* **2014**, *1* (1), 87-105; (b) Lee, J.-S.; Lee, S.-K.; Kim, B.-S.; Im, G.-I.; Cho, K.-S.; Kim, C.-S., Controlled release of BMP-2 using a heparin-conjugated carrier system reduces in vivo adipose tissue formation. *Journal of Biomedical Materials Research Part A* **2015**, *103* (2), 545-554.
69. (a) Norouzi, M.; Shabani, I.; Ahvaz, H. H.; Soleimani, M., PLGA/gelatin hybrid nanofibrous scaffolds encapsulating EGF for skin regeneration. *Journal of Biomedical Materials Research Part A* **2015**, *103* (7), 2225-2235; (b) Tamama, K.; Kawasaki, H.; Wells, A., Epidermal Growth Factor (EGF) Treatment on Multipotential Stromal Cells (MSCs). Possible Enhancement of Therapeutic Potential of MSC. *Journal of Biomedicine and Biotechnology* **2010**, *2010*, 10.
70. (a) Kabiri, A.; Esfandiari, E.; Esmaeili, A.; Hashemibeni, B.; Pourazar, A.; Mardani, M., Platelet-rich plasma application in chondrogenesis. *Advanced Biomedical Research* **2014**, *3*, 138; (b) Otani, Y.; Komura, M.; Komura, H.; Ishimaru, T.; Konishi, K.; Komuro, H.; Hoshi, K.; Takato, T.; Tabata, Y.; Iwanaka, T., Optimal Amount of Basic Fibroblast Growth Factor in Gelatin Sponges Incorporating β -Tricalcium Phosphate with Chondrocytes. *Tissue Engineering. Part A* **2015**, *21* (3-4), 627-636.
71. (a) Mullen, L. M.; Best, S. M.; Ghose, S.; Wardale, J.; Rushton, N.; Cameron, R. E., Bioactive IGF-1 release from collagen-GAG scaffold to enhance cartilage repair in vitro. *Journal of Materials Science: Materials in Medicine* **2015**, *26* (1), 1-8; (b) Locatelli, V.; Bianchi, V. E., Effect of GH/IGF-1 on Bone Metabolism and Osteoporosis. *International Journal of Endocrinology* **2014**, *2014*, 25.
72. Chao, X.; Xu, L.; Li, J.; Han, Y.; Li, X.; Mao, Y.; Shang, H.; Fan, Z.; Wang, H., Facilitation of facial nerve regeneration using chitosan- β -glycerophosphate-nerve growth factor hydrogel. *Acta Oto-Laryngologica* **2016**, *136* (6), 585-591.
73. Dai, N.; Yasuhiko, T.; Soh, S., Periodontal tissue regeneration with PRP incorporated gelatin hydrogel sponges. *Biomedical Materials* **2015**, *10* (5), 055016.
74. Li, F.; Liu, X.; Zhao, S.; Wu, H.; Xu, H. H. K., Porous chitosan bilayer membrane containing TGF- β 1 loaded microspheres for pulp capping and reparative dentin formation in a dog model. *Dental Materials* **2014**, *30* (2), 172-181.
75. (a) Freudenberg, U.; Zieris, A.; Chwalek, K.; Tsurkan, M. V.; Maitz, M. F.; Atallah, P.; Levental, K. R.; Eming, S. A.; Werner, C., Heparin desulfation modulates VEGF release and angiogenesis in diabetic wounds. *Journal of Controlled Release* **2015**, *220*, Part A, 79-88; (b) Secord, A. A.; Nixon, A. B.; Hurwitz, H. I., The search for biomarkers to direct antiangiogenic treatment in epithelial ovarian cancer. *Gynecologic Oncology* **2014**, *135* (2), 349-358.

76. (a) Stamatialis, D. F.; Papenburg, B. J.; Gironés, M.; Saiful, S.; Bettahalli, S. N. M.; Schmitmeier, S.; Wessling, M., Medical applications of membranes: Drug delivery, artificial organs and tissue engineering. *Journal of Membrane Science* **2008**, *308* (1–2), 1-34; (b) Silva, S. S.; Mano, J. F.; Reis, R. L., Soft Constructs for Skin Tissue Engineering. In *Biomimetic Approaches for Biomaterials Development*, Wiley-VCH Verlag GmbH & Co. KGaA: 2012; pp 537-557.
77. Suntornnond, R.; An, J.; Yeong, W. Y.; Chua, C. K., Biodegradable Polymeric Films and Membranes Processing and Forming for Tissue Engineering. *Macromolecular Materials and Engineering* **2015**, *300* (9), 858-877.
78. Silva, S. S.; Luna, S. M.; Gomes, M. E.; Benesch, J.; Pashkuleva, I.; Mano, J. F.; Reis, R. L., Plasma Surface Modification of Chitosan Membranes: Characterization and Preliminary Cell Response Studies. *Macromolecular Bioscience* **2008**, *8* (6), 568-576.
79. Lopez-Perez, P. M.; Marques, A. P.; Silva, R. M. P. d.; Pashkuleva, I.; Reis, R. L., Effect of chitosan membrane surface modification via plasma induced polymerization on the adhesion of osteoblast-like cells. *Journal of Materials Chemistry* **2007**, *17* (38), 4064-4071.
80. (a) Monteiro, N.; Martins, A.; Reis, R. L.; Neves, N. M., Nanoparticle-based bioactive agent release systems for bone and cartilage tissue engineering. *Regenerative Therapy* **2015**, *1*, 109-118; (b) Shi, J.; Votruba, A. R.; Farokhzad, O. C.; Langer, R., Nanotechnology in drug delivery and tissue engineering: From discovery to applications. *Nano Letters* **2010**, *10* (9), 3223-3230.
81. Stendahl, J. C.; Sinusas, A. J., Nanoparticles for Cardiovascular Imaging and Therapeutic Delivery, Part 1: Compositions and Features. *J. Nucl. Med.* **2015**, *56* (10), 1469-1475.
82. Santo, V.; Ratanavaraporn, J.; Sato, K.; Gomes, M.; Mano, J.; Reis, R.; Tabata, Y., Cell engineering by the internalization of bioinstructive micelles for enhanced bone regeneration. *Nanomedicine-Uk* **2015**, *10*, 1707-1721.
83. (a) Quinlan, E.; López-Noriega, A.; Thompson, E.; Kelly, H. M.; Cryan, S. A.; O'Brien, F. J., Development of collagen–hydroxyapatite scaffolds incorporating PLGA and alginate microparticles for the controlled delivery of rhBMP-2 for bone tissue engineering. *Journal of Controlled Release* **2015**, *198*, 71-79; (b) Gentile, P.; Nandagiri, V. K.; Daly, J.; Chiono, V.; Mattu, C.; Tonda-Turo, C.; Ciardelli, G.; Ramtoola, Z., Localised controlled release of simvastatin from porous chitosan–gelatin scaffolds engrafted with simvastatin loaded PLGA-microparticles for bone tissue engineering application. *Materials Science and Engineering: C* **2016**, *59*, 249-257.
84. Kohane, D. S., Microparticles and nanoparticles for drug delivery. *Biotechnology and Bioengineering* **2007**, *96* (2), 203-209.
85. Subbiah, R.; Veerapandian M Fau - Yun, K. S.; Yun, K. S., Nanoparticles: functionalization and multifunctional applications in biomedical sciences. **2010**, *17* (36), 4559 - 4577.
86. Kamaly, N.; Xiao, Z.; Valencia, P.; Radovic-Morenob, A.; Farokhzad, O., Targeted polymeric therapeutic nanoparticles: design, development and clinical translation. *Chem. Soc. Rev.* **2012**, *41*, 2971-3010.
87. Locatelli, E.; Franchini, M. C., Polymeric Nanoparticles: Description, Synthesis and Applications. *Isotopes in Nanoparticles: Fundamentals and Applications* **2016**, 113.
88. (a) Tonello, S.; Moore, M. C.; Sharma, B.; Dobson, J.; McFetridge, P. S., Controlled release of a heterogeneous human placental matrix from PLGA microparticles to modulate angiogenesis. *Drug delivery and translational research* **2016**, *6* (2), 174-183; (b) Raftery, R. M.; Tierney, E. G.; Curtin, C. M.; Cryan, S.-A.; O'Brien, F. J., Development of a gene-activated scaffold platform for tissue engineering applications

using chitosan-pDNA nanoparticles on collagen-based scaffolds. *Journal of Controlled Release* **2015**, *210*, 84-94.

89. (a) Heidari, F.; Bahrololoom, M. E.; Vashae, D.; Tayebi, L., In situ preparation of iron oxide nanoparticles in natural hydroxyapatite/chitosan matrix for bone tissue engineering application. *Ceramics International* **2015**, *41* (2, Part B), 3094-3100; (b) Hickey, D. J.; Ercan, B.; Sun, L.; Webster, T. J., Adding MgO nanoparticles to hydroxyapatite-PLLA nanocomposites for improved bone tissue engineering applications. *Acta biomaterialia* **2015**, *14*, 175-184; (c) Mehrasa, M.; Asadollahi, M. A.; Ghaedi, K.; Salehi, H.; Arpanaei, A., Electrospun aligned PLGA and PLGA/gelatin nanofibers embedded with silica nanoparticles for tissue engineering. *International journal of biological macromolecules* **2015**, *79*, 687-695.

90. Gil, S.; Correia, C. R.; Mano, J. F., Magnetically Labeled Cells with Surface-Modified Fe₃O₄ Spherical and Rod-Shaped Magnetic Nanoparticles for Tissue Engineering Applications. *Advanced healthcare materials* **2015**, *4* (6), 883-891.

91. (a) Vieira, S.; Vial, S.; Maia, F.; Carvalho, M.; Reis, R.; Granja, P.; Oliveira, J., Gellan gum-coated gold nanorods: an intracellular nanosystem for bone tissue engineering *RSC Adv* **2015**, *5*, 77996-78005; (b) Vial, S.; Reis, R. L.; Oliveira, J. M., Recent advances using gold nanoparticles as a promising multimodal tool for tissue engineering and regenerative medicine. *Current Opinion in Solid State and Materials Science* **2016**.

92. Hasani-Sadrabadi, M. M.; Pour Hajrezaei, S.; Hojjati Emami, S.; Bahlakeh, G.; Daneshmandi, L.; Dashtimoghadam, E.; Seyedjafari, E.; Jacob, K. I.; Tayebi, L., Enhanced osteogenic differentiation of stem cells *via* microfluidics synthesized nanoparticles. *Nanomedicine: Nanotechnology, Biology and Medicine* **2015**, *11* (7), 1809-1819.

93. Park, M.; Lee, D.; Shin, S.; Hyun, J., Effect of negatively charged cellulose nanofibers on the dispersion of hydroxyapatite nanoparticles for scaffolds in bone tissue engineering. *Colloids and Surfaces B: Biointerfaces* **2015**, *130*, 222-228.

94. Luo, Z.; Deng, Y.; Zhang, R.; Wang, M.; Bai, Y.; Zhao, Q.; Lyu, Y.; Wei, J.; Wei, S., Peptide-laden mesoporous silica nanoparticles with promoted bioactivity and osteo-differentiation ability for bone tissue engineering. *Colloids and Surfaces B: Biointerfaces* **2015**, *131*, 73-82.

95. Chen, J.-P.; Tsai, M.-J.; Liao, H.-T., Incorporation of biphasic calcium phosphate microparticles in injectable thermoresponsive hydrogel modulates bone cell proliferation and differentiation. *Colloids and Surfaces B: Biointerfaces* **2013**, *110*, 120-129.

96. Wang, Y.; Zhang, Y.; Wang, B.; Cao, Y.; Yu, Q.; Yin, T., Fabrication of core-shell micro/nanoparticles for programmable dual drug release by emulsion electrospraying. *Journal of Nanoparticle Research* **2013**, *15* (6), 1-12.

97. (a) Othman, R.; Vladislavljević, G. T.; Thomas, N. L.; Nagy, Z. K., Fabrication of composite poly (D, L-lactide)/montmorillonite nanoparticles for controlled delivery of acetaminophen by solvent-displacement method using glass capillary microfluidics. *Colloids and Surfaces B: Biointerfaces* **2016**, *141*, 187-195; (b) Wu, X.; Chang, Y.; Fu, Y.; Ren, L.; Tong, J.; Zhou, J., Effects of non-solvent and starch solution on formation of starch nanoparticles by nanoprecipitation. *Starch - Stärke* **2016**, *68* (3-4), 258-263.

98. Esmaeili, F.; Atyabi, F.; Dinarvand, R., Preparation and characterization of estradiol-loaded PLGA nanoparticles using homogenization-solvent diffusion method. *DARU Journal of Pharmaceutical Sciences* **2015**, *16* (4), 196-202.

99. Fan, J. P.; Kalia, P.; Di Silvio, L.; Huang, J., In vitro response of human osteoblasts to multi-step sol-gel derived bioactive glass nanoparticles for bone tissue engineering. *Materials Science and Engineering: C* **2014**, *36*, 206-214.

100. Duarte, A. R. C.; Mano, J. F.; Reis, R. L., Polymer Processing Using Supercritical Fluid-Based Technologies for Drug Delivery and Tissue Engineering Applications. *Supercritical Fluid Nanotechnology: Advances and Applications in Composites and Hybrid Nanomaterials* **2015**, 273.
101. Kim, Y.; Langer, R., Microfluidics in Nanomedicine. *Reviews in Cell Biology and Molecular Medicine* **2015**.
102. Jayaraman, P.; Gandhimathi, C.; Venugopal, J. R.; Becker, D. L.; Ramakrishna, S.; Srinivasan, D. K., Controlled release of drugs in electrosprayed nanoparticles for bone tissue engineering. *Advanced Drug Delivery Reviews* **2015**, *94*, 77-95.
103. Bock, N.; Woodruff, M.; Hutmacher, D.; Dargaville, T., Electrospraying, a Reproducible Method for Production of Polymeric Microspheres for Biomedical Applications *Polymers* **2011**, *3*, 131-149.
104. (a) Ebrahimgol, F.; Tavanai, H.; Alihosseini, F.; Khayamian, T., Electrosprayed recovered wool keratin nanoparticles. *Polym. Adv. Technol.* **2014**, *25* (9), 1001-1007; (b) Xie, J.; Jiang, J.; Davoodi, P.; Srinivasan, M. P.; Wang, C. H., Electrohydrodynamic atomization: A two-decade effort to produce and process micro-/nanoparticulate materials. *Chemical Engineering Science* **2015**, *125*, 32-57.
105. Lima, A. C.; Song W Fau - Blanco-Fernandez, B.; Blanco-Fernandez B Fau - Alvarez-Lorenzo, C.; Alvarez-Lorenzo C Fau - Mano, J. F.; Mano, J. F., Synthesis of temperature-responsive dextran-MA/PNIPAAm particles for controlled drug delivery using superhydrophobic surfaces. *Pharmaceutical Research* **2011**, *28* (6), 1294-1305.
106. Xue, C.-H.; Jia, S.-T.; Zhang, J.; Ma, J.-Z., Large-area fabrication of superhydrophobic surfaces for practical applications: an overview. *Science and Technology of Advanced Materials* **2016**.
107. Langer, R.; Tirrell, D. A., Designing materials for biology and medicine. *Nature* **2004**, *428* (6982), 487-492.
108. Thorrez, L.; Shansky, J.; Wang, L.; Fast, L.; VandenDriessche, T.; Chuah, M.; Mooney, D.; Vandenburgh, H., Growth, differentiation, transplantation and survival of human skeletal myofibers on biodegradable scaffolds. *Biomaterials* **2008**, *29* (1), 75-84.
109. Yan, L.; Salgado, A.; Oliveira, J.; Oliveira, A.; Reis, R., De novo bone formation on macro/microporous silk and silk/nano-sized calcium phosphate scaffolds. *J Bioact Comp Pol* **2013**, *28*, 439-452.
110. Castilho, M.; Rodrigues, J.; Pires, I.; Gouveia, B.; Pereira, M.; Moseke, C.; Groll, J.; Ewald, A.; Vorndran, E., Fabrication of individual alginate-TCP scaffolds for bone tissue engineering by means of powder printing. *Biofabrication* **2015**, *7* (1), 015004.
111. Pina, S.; Oliveira, J. M.; Reis, R. L., Natural-Based Nanocomposites for Bone Tissue Engineering and Regenerative Medicine: A Review. *Advanced Materials* **2015**, *27* (7), 1143-1169.
112. Oliveira, J.; Silva, S.; Malafaya, P.; Rodrigues, M.; Kotobuki, N.; Hirose, M.; Reis, R., Macroporous hydroxyapatite scaffolds for bone tissue engineering applications: Physicochemical characterization and assessment of rat bone marrow stromal cell viability. *Inc J Biomed Mater Res A* **2009**, *91*, 175-86.
113. Hou, Q.; Grijpma, D.; Feijen, J., Porous polymeric structures for tissue engineering prepared by a coagulation, compression moulding and salt leaching technique. *Biomaterials* **2003**, *24*, 1937-47.
114. Yan, L.; Oliveira, J.; Oliveira, A.; Reis, R., Silk Fibroin/Nano-CaP Bilayered scaffolds for Osteochondral Tissue Engineering. *Key Eng Mater* **2014**, *587*, 245.
115. vandeWitte, P.; Dijkstra, P.; vandenBerg, J.; Feijen, J., Phase separation processes in polymer solutions in relation to membrane formation. *J Memb Sci* **1996**, *117*, 1-31.

116. Dehghani, F.; Annabi, N., Engineering porous scaffolds using gas-based techniques. *Current opinion in biotechnology* **2011**, *22*, 661-6.
117. (a) Cui, L.; Zhang, N.; Cui, W.; Zhang, P.; Chen, X., A novel nano/micro-fibrous scaffold by melt-spinning method for bone tissue engineering. *Journal of Bionic Engineering* **2015**, *12* (1), 117-128; (b) Cardea, S.; Scognamiglio, M.; Reverchon, E., Supercritical fluid assisted process for the generation of cellulose acetate loaded structures, potentially useful for tissue engineering applications. *Materials Science and Engineering: C* **2016**, *59*, 480-487.
118. Chae, T.; Yang, H.; Leung, V.; Ko, F.; Troczynski, T., Novel biomimetic hydroxyapatite/alginate nanocomposite fibrous scaffolds for bone tissue regeneration. *J Mater Sci Mater Med* **2013**, *24*, 1885-94.
119. Barbani, N.; Guerra, G.; Cristallini, C.; Urciuoli, P.; Avvisati, R.; Sala, A., Hydroxyapatite/gelatin/gellan sponges as nanocomposite scaffolds for bone reconstruction. *J Mater Sci Mater Med* **2012**, *23*, 51-61.
120. Martínez-Vázquez, F.; Cabanas, M.; Paris, J.; Lozano, D.; Vallet-Regí, M., Fabrication of novel Si-doped hydroxyapatite/gelatine scaffolds by rapid prototyping for drug delivery and bone regeneration. *Acta biomaterialia* **2015**, *15*, 200-209.
121. Yan, L.-P.; Silva-Correia, J.; Oliveira, M. B.; Vilela, C.; Pereira, H.; Sousa, R. A.; Mano, J. F.; Oliveira, A. L.; Oliveira, J. M.; Reis, R. L., Bilayered silk/silk-nanoCaP scaffolds for osteochondral tissue engineering: In vitro and in vivo assessment of biological performance. *Acta biomaterialia* **2015**, *12*, 227-241.
122. Peppas, N. A.; Hilt, J. Z.; Khademhosseini, A.; Langer, R., Hydrogels in Biology and Medicine: From Molecular Principles to Bionanotechnology. *Advanced Materials* **2006**, *18* (11), 1345-1360.
123. (a) Wang, H.; Heilshorn, S. C., Adaptable Hydrogel Networks with Reversible Linkages for Tissue Engineering. *Advanced Materials* **2015**, *27* (25), 3717-3736; (b) Toh, W. S.; Loh, X. J., Advances in hydrogel delivery systems for tissue regeneration. *Materials Science & Engineering C-Materials for Biological Applications* **2014**, *45*, 690-697; (c) Utech, S.; Boccaccini, A. R., A review of hydrogel-based composites for biomedical applications: enhancement of hydrogel properties by addition of rigid inorganic fillers. *Journal of Materials Science* **2016**, *51* (1), 271-310.
124. Chua, C. K.; Yeong, W. Y., *Bioprinting: Principles and Applications*. Word Scientific Publishing Co.: 2014; p 296.
125. (a) Hadjipanayi, E.; Ananta, M.; Binkowski, M.; Streeter, I.; Lu, Z.; Cui, Z. F.; Brown, R. A.; Mudera, V., Mechanisms of structure generation during plastic compression of nanofibrillar collagen hydrogel scaffolds: towards engineering of collagen. *Journal of tissue engineering and regenerative medicine* **2011**, *5* (7), 505-519; (b) Chicatun, F.; Muja, N.; Serpooshan, V.; Quinn, T. M.; Nazhat, S. N., Effect of chitosan incorporation on the consolidation process of highly hydrated collagen hydrogel scaffolds. *Soft Matter* **2013**, *9* (45), 10811-10821.
126. (a) Popa, E. G.; Gomes, M. E.; Reis, R. L., Cell Delivery Systems Using Alginate-Carrageenan Hydrogel Beads and Fibers for Regenerative Medicine Applications. *Biomacromolecules* **2011**, *12* (11), 3952-3961; (b) Zehnder, T.; Sarker, B.; Boccaccini, A. R.; Detsch, R., Evaluation of an alginate-gelatine crosslinked hydrogel for bioplotting. *Biofabrication* **2015**, *7* (2); (c) Aguado, B. A.; Mulyasmita, W.; Su, J.; Lampe, K. J.; Heilshorn, S. C., Improving Viability of Stem Cells During Syringe Needle Flow Through the Design of Hydrogel Cell Carriers. *Tissue Eng Pt A* **2012**, *18* (7-8), 806-815.
127. (a) Camci-Unal, G.; Nichol, J. W.; Bae, H.; Tekin, H.; Bischoff, J.; Khademhosseini, A., Hydrogel surfaces to promote attachment and spreading of endothelial progenitor cells. *Journal of tissue engineering and regenerative medicine*

- 2013**, 7 (5), 337-347; (b) Lam, J.; Truong, N. F.; Segura, T., Design of cell-matrix interactions in hyaluronic acid hydrogel scaffolds. *Acta biomaterialia* **2014**, 10 (4), 1571-1580.
128. Cheng, Y.-H.; Yang, S.-H.; Lin, F.-H., Thermosensitive chitosan-gelatin-glycerol phosphate hydrogel as a controlled release system of ferulic acid for nucleus pulposus regeneration. *Biomaterials* **2011**, 32 (29), 6953-6961.
129. Lin, H.; Cheng, A. W.-M.; Alexander, P. G.; Beck, A. M.; Tuan, R. S., Cartilage Tissue Engineering Application of Injectable Gelatin Hydrogel with In Situ Visible-Light-Activated Gelation Capability in Both Air and Aqueous Solution. *Tissue Eng Pt A* **2014**, 20 (17-18), 2402-2411.
130. (a) Douglas, T. E. L.; Wlodarczyk, M.; Pamula, E.; Declercq, H. A.; de Mulder, E. L. W.; Bucko, M. M.; Balcaen, L.; Vanhaecke, F.; Cornelissen, R.; Dubruel, P.; Jansen, J. A.; Leeuwenburgh, S. C. G., Enzymatic mineralization of gellan gum hydrogel for bone tissue-engineering applications and its enhancement by polydopamine. *Journal of tissue engineering and regenerative medicine* **2014**, 8 (11), 906-918; (b) Khang, G.; Lee, S. K.; Kim, H. N.; Silva-Correia, J.; Gomes, M. E.; Viegas, C. A. A.; Dias, I. R.; Oliveira, J. M.; Reis, R. L., Biological evaluation of intervertebral disc cells in different formulations of gellan gum-based hydrogels. *Journal of tissue engineering and regenerative medicine* **2015**, 9 (3), 265-275.
131. Wang, H.-Y.; Zhang, Q., Processing Silk Hydrogel and Its Applications in Biomedical Materials. *Biotechnology Progress* **2015**, 31 (3), 630-640.
132. Rufaihah, A. J.; Vaibavi, S. R.; Plotkin, M.; Shen, J.; Nithya, V.; Wang, J.; Seliktar, D.; Kofidis, T., Enhanced infarct stabilization and neovascularization mediated by VEGF-loaded PEGylated fibrinogen hydrogel in a rodent myocardial infarction model. *Biomaterials* **2013**, 34 (33), 8195-8202.
133. (a) Radhakrishnan, J.; Krishnan, U. M.; Sethuraman, S., Hydrogel based injectable scaffolds for cardiac tissue regeneration. *Biotechnology advances* **2014**, 32 (2), 449-461; (b) Lewandowska-Lancucka, J.; Fiejdasz, S.; Rodzik, L.; Koziel, M.; Nowakowska, M., Bioactive hydrogel-nanosilica hybrid materials: a potential injectable scaffold for bone tissue engineering. *Biomedical Materials* **2015**, 10 (1).
134. (a) Lin, R.-Z.; Chen, Y.-C.; Moreno-Luna, R.; Khademhosseini, A.; Melero-Martin, J. M., Transdermal regulation of vascular network bioengineering using a photopolymerizable methacrylated gelatin hydrogel. *Biomaterials* **2013**, 34 (28), 6785-6796; (b) Killion, J. A.; Geever, L. M.; Devine, D. M.; Higginbotham, C. L., Fabrication and invitro biological evaluation of photopolymerisable hydroxyapatite hydrogel composites for bone regeneration. *Journal of Biomaterials Applications* **2014**, 28 (8), 1274-1283; (c) Douglas, T. E. L.; Piwowarczyk, W.; Pamula, E.; Liskova, J.; Schaubroeck, D.; Leeuwenburgh, S. C. G.; Brackman, G.; Balcaen, L.; Detsch, R.; Declercq, H.; Cholewa-Kowalska, K.; Dokupil, A.; Cuijpers, V. M. J. I.; Vanhaecke, F.; Cornelissen, R.; Coenye, T.; Boccaccini, A. R.; Dubruel, P., Injectable self-gelling composites for bone tissue engineering based on gellan gum hydrogel enriched with different bioglasses. *Biomedical Materials* **2014**, 9 (4).
135. Wang, X.; Hao, T.; Qu, J.; Wang, C.; Chen, H., Synthesis of Thermal Polymerizable Alginate-GMA Hydrogel for Cell Encapsulation. *Journal of Nanomaterials* **2015**.
136. Navaei, A.; Danh, T.; Heffernan, J.; Cutts, J.; Brafman, D.; Sirianni, R. W.; Vernon, B.; Nikkhah, M., PNIPAAm-based biohybrid injectable hydrogel for cardiac tissue engineering. *Acta biomaterialia* **2016**, 32, 10-23.

137. Merceron, T. K.; Murphy, S. V., Hydrogels for 3D Bioprinting Applications (Chapter 14) - Atala, Anthony. In *Essentials of 3D Biofabrication and Translation*, Yoo, J. J., Ed. Academic Press: Boston, 2015; pp 249-270.
138. Lode, A.; Krujatz, F.; Brueggemeier, S.; Quade, M.; Schuetz, K.; Knaack, S.; Weber, J.; Bley, T.; Gelinsky, M., Green bioprinting: Fabrication of photosynthetic algae-laden hydrogel scaffolds for biotechnological and medical applications. *Engineering in Life Sciences* **2015**, *15* (2), 177-183.
139. (a) Wang, L.; Xu, M.; Zhang, L.; Zhou, Q.; Luo, L., Automated quantitative assessment of three-dimensional bioprinted hydrogel scaffolds using optical coherence tomography. *Biomedical Optics Express* **2016**, *7* (3), 894-910; (b) Zorlutuna, P.; Jeong, J. H.; Kong, H.; Bashir, R., Stereolithography-Based Hydrogel Microenvironments to Examine Cellular Interactions. *Advanced Functional Materials* **2011**, *21* (19), 3642-3651.
140. Pereira, R. F.; Bartolo, P. J., 3D bioprinting of photocrosslinkable hydrogel constructs. *J Appl Polym Sci* **2015**, *132* (48).
141. Wuest, S.; Godla, M. E.; Mueller, R.; Hofmann, S., Tunable hydrogel composite with two-step processing in combination with innovative hardware upgrade for cell-based three-dimensional bioprinting. *Acta biomaterialia* **2014**, *10* (2), 630-640.
142. Murphy, S. V.; Atala, A., 3D bioprinting of tissues and organs. *Nat Biotech* **2014**, *32* (8), 773-785.
143. (a) Vasiev, I.; Greer, A. I. M.; Khokhar, A. Z.; Stormonth-Darling, J.; Tanner, K. E.; Gadegaard, N., Self-folding nano- and micropatterned hydrogel tissue engineering scaffolds by single step photolithographic process. *Microelectronic Engineering* **2013**, *108*, 76-81; (b) Bajaj, P.; Schweller, R. M.; Khademhosseini, A.; West, J. L.; Bashir, R., 3D Biofabrication Strategies for Tissue Engineering and Regenerative Medicine. In *Annual Review of Biomedical Engineering, Vol 16*, Yarmush, M. L., Ed. 2014; Vol. 16, pp 247-276; (c) Gasperini, L.; Mano, J. F.; Reis, R. L., Natural polymers for the microencapsulation of cells. *Journal of the Royal Society Interface* **2014**, *11* (100).
144. (a) Fu, C.-Y.; Lin, C.-Y.; Chu, W.-C.; Chang, H.-Y., A Simple Cell Patterning Method Using Magnetic Particle-Containing Photosensitive Poly (Ethylene Glycol) Hydrogel Blocks: A Technical Note. *Tissue Engineering Part C-Methods* **2011**, *17* (8), 871-877; (b) Sharifi, S.; Blanquer, S. B. G.; van Kooten, T. G.; Grijpma, D. W., Biodegradable nanocomposite hydrogel structures with enhanced mechanical properties prepared by photo-crosslinking solutions of poly(trimethylene carbonate)-poly(ethylene glycol)-poly(trimethylene carbonate) macromonomers and nanoclay particles. *Acta biomaterialia* **2012**, *8* (12), 4233-4243; (c) Lee, H. J.; Koh, W. G., Hydrogel Micropattern-Incorporated Fibrous Scaffolds Capable of Sequential Growth Factor Delivery for Enhanced Osteogenesis of hMSCs. *ACS Appl. Mater. Interfaces* **2014**, *6* (12), 9338-9348.
145. Verhulsel, M.; Vignes, M.; Descroix, S.; Malaquin, L.; Vignjevic, D. M.; Viovy, J.-L., A review of microfabrication and hydrogel engineering for micro-organs on chips. *Biomaterials* **2014**, *35* (6), 1816-1832.
146. Khan, F.; Tanaka, M.; Ahmad, S. R., Fabrication of polymeric biomaterials: a strategy for tissue engineering and medical devices. *Journal of Materials Chemistry B* **2015**, *3* (42), 8224-8249.
147. You, J.; Shin, D. S.; Revzin, A., Development of Micropatterned Cell-Sensing Surfaces. In *Micropatterning in Cell Biology, Pt C*, Piel, M.; Thery, M., Eds. Elsevier Academic Press Inc: San Diego, 2014; Vol. 121, pp 75-90.
148. Wan, J., Microfluidic-Based Synthesis of Hydrogel Particles for Cell Microencapsulation and Cell-Based Drug Delivery. *Polymers* **2012**, *4* (2), 1084-1108.

149. Yajima, Y.; Yamada, M.; Yamada, E.; Iwase, M.; Seki, M., Facile fabrication processes for hydrogel-based microfluidic devices made of natural biopolymers. *Biomicrofluidics* **2014**, *8* (2).
150. (a) Fang, K.; Hou, C.; Huang, C.; Luo, X.; Zhang, S.; Shen, C.; Huo, D., The Rapid Fabrication of Hydrogel Microfluidic Chip for Cell Capture Culture and Metabolites Detection. In *Micro-Nano Technology Xiv, Pts 1-4*, Tang, F., Ed. 2013; Vol. 562-565, pp 632-636; (b) Liu, Z.; Xiao, L.; Xu, B.; Zhang, Y.; Mak, A. F. T.; Li, Y.; Man, W.-y.; Yang, M., Covalently immobilized biomolecule gradient on hydrogel surface using a gradient generating microfluidic device for a quantitative mesenchymal stem cell study. *Biomicrofluidics* **2012**, *6* (2); (c) Liu, N.; Li, P.; Liu, L.; Yu, H.; Wang, Y.; Lee, G.-B.; Li, W. J., 3-D Non-UV Digital Printing of Hydrogel Microstructures by Optically Controlled Digital Electropolymerization. *Journal of Microelectromechanical Systems* **2015**, *24* (6), 2128-2135.
151. Cosson, S.; Lutolf, M. P., Hydrogel microfluidics for the patterning of pluripotent stem cells. *Scientific Reports* **2014**, *4*, 4462.
152. Lee, D.-H.; Bae, C. Y.; Kwon, S.; Park, J.-K., User-friendly 3D bioassays with cell-containing hydrogel modules: narrowing the gap between microfluidic bioassays and clinical end-users' needs. *Lab on a Chip* **2015**, *15* (11), 2379-2387.
153. (a) Yamada, M.; Sugaya, S.; Naganuma, Y.; Seki, M., Microfluidic synthesis of chemically and physically anisotropic hydrogel microfibers for guided cell growth and networking. *Soft Matter* **2012**, *8* (11), 3122-3130; (b) Chung, B. G.; Lee, K.-H.; Khademhosseini, A.; Lee, S.-H., Microfluidic fabrication of microengineered hydrogels and their application in tissue engineering. *Lab on a Chip* **2012**, *12* (1), 45-59.
154. Ghorbanian, S.; Qasaimeh, M. A.; Akbari, M.; Tamayol, A.; Juncker, D., Microfluidic direct writer with integrated declogging mechanism for fabricating cell-laden hydrogel constructs. *Biomedical Microdevices* **2014**, *16* (3), 387-395.
155. Correia, C. R.; Pirraco, R. P.; Cerqueira, M. T.; Marques, A. P.; Reis, R. L.; Mano, J. F., Semipermeable Capsules Wrapping a Multifunctional and Self-regulated Co-culture Microenvironment for Osteogenic Differentiation. *Scientific Reports* **2016**, *6*, 21883.
156. Kang, A.; Park, J.; Ju, J.; Jeong, G. S.; Lee, S.-H., Cell encapsulation via microtechnologies. *Biomaterials* **2014**, *35*, 2651-2663.
157. Malda, J.; Visser, J.; Melchels, F. P.; Jüngst, T.; Hennink, W. E.; Dhert, W. J. A.; Groll, J.; Huttmacher, D. W., 25th anniversary article: Engineering hydrogels for biofabrication. *Advanced Materials* **2013**, *25*, 5011-5028.
158. Gurruchaga, H.; Saenz Del Burgo, L.; Ciriza, J.; Orive, G.; Hernández, R. M.; Pedraz, J. L., Advances in cell encapsulation technology and its application in drug delivery. *Expert opinion on drug delivery* **2015**, *5247*, 1-17.
159. Swioklo, S.; Constantinescu, A.; Connon, C. J., Alginate-Encapsulation for the Improved Hypothermic Preservation of Human Adipose-Derived Stem Cells. *Stem Cells Translational Medicine* **2016**, *5*, 339-349.
160. Kharkar, P. M.; Kiick, K. L.; Kloxin, A. M., Designing degradable hydrogels for orthogonal control of cell microenvironments. *Chemical Society reviews* **2013**, *42*, 7335-72.
161. (a) Uludag, H.; De Vos, P.; Tresco, P. A., Technology of mammalian cell encapsulation. In *Advanced Drug Delivery Reviews*, 2000; Vol. 42, pp 29-64; (b) Gasperini, L.; Mano, J. F.; Reis, R. L., Natural polymers for the microencapsulation of cells. *Journal of The Royal Society Interface* **2014**, *11*, 20140817-20140817.
162. Rokstad, A. M. A.; Lacík, I.; de Vos, P.; Strand, B. L., Advances in biocompatibility and physico-chemical characterization of microspheres for cell encapsulation. *Advanced drug delivery reviews* **2014**, *67-68*, 111-30.

163. De Vos, P.; Spasojevic, M.; Faas, M. M., Treatment of diabetes with encapsulated islets. *Advances in Experimental Medicine and Biology* **2010**, 670, 38-53.
164. Nafea, E. H.; Poole-Warren, A. M. L. A.; Martens, P. J., Immunisolating semi-permeable membranes for cell encapsulation: Focus on hydrogels. In *Journal of Controlled Release*, 2011; Vol. 154, pp 110-122.
165. Bhujbal, S. V.; de Haan, B.; Niclou, S. P.; de Vos, P., A novel multilayer immunisolating encapsulation system overcoming protrusion of cells. *Scientific Reports* **2014**, 4, 6856.
166. Mayfield, A. E.; Tilokee, E. L.; Latham, N.; McNeill, B.; Lam, B. K.; Ruel, M.; Suuronen, E. J.; Courtman, D. W.; Stewart, D. J.; Davis, D. R., The effect of encapsulation of cardiac stem cells within matrix-enriched hydrogel capsules on cell survival, post-ischemic cell retention and cardiac function. *Biomaterials* **2014**, 35, 133-142.
167. (a) Balyura, M.; Gelfgat, E.; Ehrhart-Bornstein, M.; Ludwig, B.; Gendler, Z.; Barkai, U.; Zimerman, B.; Rotem, A.; Block, N. L.; Schally, A. V.; Bornstein, S. R., Transplantation of bovine adrenocortical cells encapsulated in alginate. *Proceedings of the National Academy of Sciences* **2015**, 112 2527-2532; (b) Song, W.; Lu, Y.-C.; Frankel, A. S.; An, D.; Schwartz, R. E.; Ma, M., Engraftment of human induced pluripotent stem cell-derived hepatocytes in immunocompetent mice via 3D co-aggregation and encapsulation. *Scientific reports* **2015**, 5, 16884.
168. Stucky, E. C.; Schloss, R. S.; Yarmush, M. L.; Shreiber, D. I., Alginate micro-encapsulation of mesenchymal stromal cells enhances modulation of the neuro-inflammatory response. *Cytotherapy* **2015**, 17, 1353-1364.
169. (a) Steele, J. A. M.; Hallé, J.-P.; Poncelet, D.; Neufeld, R. J., Therapeutic cell encapsulation techniques and applications in diabetes. *Advanced drug delivery reviews* **2014**, 67-68, 74-83; (b) Yang, H. K.; Yoon, K.-H. H., Current status of encapsulated islet transplantation. *Journal of Diabetes and its Complications* **2015**, 29, 737-743.
170. Lim, F.; Sun, A. M., Microencapsulated islets as bioartificial endocrine pancreas. *Science (New York, N.Y.)* **1980**, 210, 908-910.
171. Hamilton, D. C.; Shih, H. H.; Schubert, R. A.; Michie, S. A.; Staats, P. N.; Kaplan, D. L.; Fontaine, M. J., A silk-based encapsulation platform for pancreatic islet transplantation improves islet function in vivo. *Journal of tissue engineering and regenerative medicine* **2015**, n/a-n/a.
172. Scharp, D. W.; Marchetti, P., Encapsulated islets for diabetes therapy: history, current progress, and critical issues requiring solution. *Advanced drug delivery reviews* **2014**, 67-68, 35-73.
173. Tuch, B. E.; Keogh, G. W.; Williams, L. J.; Wu, W.; Foster, J. L.; Vaithilingam, V.; Philips, R., Safety and viability of microencapsulated human islets transplanted into diabetic humans. *Diabetes Care* **2009**, 32, 1887-1889.
174. Vegas, A. J.; Veiseh, O.; Gürtler, M.; Millman, J. R.; Pagliuca, F. W.; Bader, A. R.; Doloff, J. C.; Li, J.; Chen, M.; Olejnik, K.; Tam, H. H.; Jhunjhunwala, S.; Langan, E.; Aresta-Dasilva, S.; Gandham, S.; McGarrigle, J. J.; Bochenek, M. A.; Hollister-Lock, J.; Oberholzer, J.; Greiner, D. L.; Weir, G. C.; Melton, D. A.; Langer, R.; Anderson, D. G., Long-term glycemic control using polymer-encapsulated human stem cell-derived beta cells in immune-competent mice. *Nature Medicine* **2016**, 22, 306-311.
175. Heathman, T. R.; Nienow, A. W.; McCall, M. J.; Coopman, K.; Kara, B.; Hewitt, C. J., The translation of cell-based therapies: clinical landscape and manufacturing challenges. *Regenerative Medicine* **2015**, 10, 49-64.

176. Wilson, J. L.; Mcdevitt, T. C., Stem cell microencapsulation for phenotypic control, bioprocessing, and transplantation. *Biotechnology and Bioengineering* **2013**, *110*, 667-682.
177. Mahler, S.; Desille, M.; Frémond, B.; Chesné, C.; Guillouzo, A.; Campion, J.-P.; Clément, B., Hypothermic storage and cryopreservation of hepatocytes: the protective effect of alginate gel against cell damages. *Cell transplantation* **2003**, *12*, 579-92.
178. Mayer, F. Q.; Baldo, G.; de Carvalho, T. G.; Lagranha, V. L.; Giugliani, R.; Matte, U., Effects of cryopreservation and hypothermic storage on cell viability and enzyme activity in recombinant encapsulated cells overexpressing alpha-L-iduronidase. *Artificial organs* **2010**, *34*, 434-9.
179. Chen, B.; Wright, B.; Sahoo, R.; Connon, C. J., A Novel Alternative to Cryopreservation for the Short-Term Storage of Stem Cells for Use in Cell Therapy Using Alginate Encapsulation. *Tissue Engineering Part C: Methods* **2013**, *19*, 568-576.
180. Wright, B.; Cave, R. A.; Cook, J. P.; Khutoryanskiy, V. V.; Mi, S.; Chen, B.; Leyland, M.; Connon, C. J., Enhanced viability of corneal epithelial cells for efficient transport/storage using a structurally modified calcium alginate hydrogel. *Regenerative Medicine* **2012**, *7*, 295-307.
181. (a) Nicodemus, G. D.; Bryant, S. J., Cell Encapsulation in Biodegradable Hydrogels for Tissue Engineering Applications. *Tissue Engineering Part B: Reviews* **2008**, *14*, 149-165; (b) Santos, E.; Pedraz, J. L.; Hernández, R. M.; Orive, G., Therapeutic cell encapsulation: Ten steps towards clinical translation. *Journal of Controlled Release* **2013**, *170*, 1-14.
182. Silva, R.; Fabry, B.; Boccaccini, A. R., Fibrous protein-based hydrogels for cell encapsulation. *Biomaterials* **2014**, *35*, 6727-6738.
183. (a) Liu, J.; Xu, H. H. K.; Zhou, H.; Weir, M. D.; Chen, Q.; Trotman, C. A., Human umbilical cord stem cell encapsulation in novel macroporous and injectable fibrin for muscle tissue engineering. *Acta biomaterialia* **2013**, *9*, 4688-4697; (b) Mak, W. C.; Olesen, K.; Sivlér, P.; Lee, C. J.; Moreno-Jimenez, I.; Edin, J.; Courtman, D.; Skog, M.; Griffith, M., Controlled Delivery of Human Cells by Temperature Responsive Microcapsules. *Journal of Functional Biomaterials* **2015**, *6*, 439-453.
184. Lü, S.; Gao, C.; Xu, X.; Bai, X.; Duan, H.; Gao, N.; Feng, C.; Xiong, Y.; Liu, M., Injectable and Self-Healing Carbohydrate-Based Hydrogel for Cell Encapsulation. *ACS Appl. Mater. Interfaces* **2015**, *7*, 13029-13037.
185. Draghi, L.; Brunelli, D.; Farè, S.; Tanzi, M. C., Programmed cell delivery from biodegradable microcapsules for tissue repair. *Journal of Biomaterials Science, Polymer Edition* **2015**, *26*, 1002-1012.
186. (a) Liu, H.; Liu, J.; Qi, C.; Fang, Y.; Zhang, L.; Zhuo, R.; Jiang, X., Thermosensitive injectable in-situ forming carboxymethyl chitin hydrogel for three-dimensional cell culture. *Acta biomaterialia* **2016**, *35*, 228-237; (b) Popa, E. G.; Caridade, S. G.; Mano, J. F.; Reis, R. L.; Gomes, M. E., Chondrogenic potential of injectable κ -carrageenan hydrogel with encapsulated adipose stem cells for cartilage tissue-engineering applications. *Journal of tissue engineering and regenerative medicine* **2015**, *9*, 550-563; (c) Wang, K.; Nune, K. C.; Misra, R. D. K., The functional response of alginate-gelatin-nanocrystalline cellulose injectable hydrogels toward delivery of cells and bioactive molecules. *Acta biomaterialia* **2016**, *36*, 143-151.
187. Silva-Correia, J.; Correia, S. I.; Oliveira, J. M.; Reis, R. L., Tissue engineering strategies applied in the regeneration of the human intervertebral disk. *Biotechnology advances* **2013**, *31* (8), 1514-1531.

188. Bertagnoli, R.; Sabatino, C. T.; Edwards, J. T.; Gontarz, G. A.; Prewett, A.; Parsons, J. R., Mechanical testing of a novel hydrogel nucleus replacement implant. *The spine journal : official journal of the North American Spine Society* **2005**, *5* (6), 672-81.
189. Boyd, L. M.; Carter, A. J., Injectable biomaterials and vertebral endplate treatment for repair and regeneration of the intervertebral disc. *European Spine Journal* **2006**, *15* (3), 414-421.
190. Wilke, H.-J.; Heuer, F.; Neidlinger-Wilke, C.; Claes, L., Is a collagen scaffold for a tissue engineered nucleus replacement capable of restoring disc height and stability in an animal model? *European Spine Journal* **2006**, *15* (3), 433-438.
191. Van Tomme, S. R.; Storm, G.; Hennink, W. E., In situ gelling hydrogels for pharmaceutical and biomedical applications. *International Journal of Pharmaceutics* **2008**, *355* (1-2), 1-18.
192. Roughley, P.; Hoemann, C.; DesRosiers, E.; Mwale, F.; Antoniou, J.; Alini, M., The potential of chitosan-based gels containing intervertebral disc cells for nucleus pulposus supplementation. *Biomaterials* **2006**, *27* (3), 388-396.
193. Périé, D.; Korda, D.; Iatridis, J. C., Confined compression experiments on bovine nucleus pulposus and annulus fibrosus: sensitivity of the experiment in the determination of compressive modulus and hydraulic permeability. *Journal of Biomechanics* *38* (11), 2164-2171.
194. Alsberg, E.; Kong, H. J.; Hirano, Y.; Smith, M. K.; Albeiruti, A.; Mooney, D. J., Regulating Bone Formation via Controlled Scaffold Degradation. *Journal of Dental Research* **2003**, *82* (11), 903-908.
195. (a) Shogren, R. L.; Bagley, E. B., Natural Polymers as Advanced Materials: Some Research Needs and Directions. In *Biopolymers*, American Chemical Society: 1999; Vol. 723, pp 2-11; (b) Malafaya, P. B.; Silva, G. A.; Reis, R. L., Natural-origin polymers as carriers and scaffolds for biomolecules and cell delivery in tissue engineering applications. *Advanced Drug Delivery Reviews* **2007**, *59* (4-5), 207-233; (c) Puppi, D.; Chiellini, F.; Piras, A. M.; Chiellini, E., Polymeric materials for bone and cartilage repair. *Progress in Polymer Science* **2010**, *35* (4), 403-440.
196. Temenoff, J. S.; Mikos, A. G., Review: tissue engineering for regeneration of articular cartilage. *Biomaterials* **2000**, *21* (5), 431-440.
197. (a) Varghese, S.; Elisseeff, J. H., Hydrogels for Musculoskeletal Tissue Engineering. In *Polymers for Regenerative Medicine*, Werner, C., Ed. Springer Berlin Heidelberg: Berlin, Heidelberg, 2006; pp 95-144; (b) Baer, A. E.; Wang, J. Y.; Kraus, V. B.; Setton, L. A., Collagen gene expression and mechanical properties of intervertebral disc cell-alginate cultures. *Journal of Orthopaedic Research* **2001**, *19* (1), 2-10; (c) Bron, J. L.; Vonk, L. A.; Smit, T. H.; Koenderink, G. H., Engineering alginate for intervertebral disc repair. *Journal of the Mechanical Behavior of Biomedical Materials* **2011**, *4* (7), 1196-1205; (d) Chou, A. I.; Nicoll, S. B., Characterization of photocrosslinked alginate hydrogels for nucleus pulposus cell encapsulation. *Journal of biomedical materials research. Part A* **2009**, *91* (1), 187-94; (e) Reza, A. T.; Nicoll, S. B., Characterization of novel photocrosslinked carboxymethylcellulose hydrogels for encapsulation of nucleus pulposus cells. *Acta biomaterialia* **2010**, *6* (1), 179-186; (f) Gupta, M. S.; Cooper, E. S.; Nicoll, S. B., Transforming Growth Factor-Beta 3 Stimulates Cartilage Matrix Elaboration by Human Marrow-Derived Stromal Cells Encapsulated in Photocrosslinked Carboxymethylcellulose Hydrogels: Potential for Nucleus Pulposus Replacement. *Tissue Eng Pt A* **2011**, *17* (23-24), 2903-2910; (g) Berger, J.; Reist, M.; Mayer, J. M.; Felt, O.; Gurny, R., Structure and interactions in chitosan hydrogels formed by complexation or aggregation for biomedical applications. *European Journal of Pharmaceutics and Biopharmaceutics* **2004**, *57* (1), 35-52; (h) Calderon, L.; Collin, E.; Velasco-Bayon, D.;

Murphy, M.; O'Halloran, D.; Pandit, A., Type II collagen-hyaluronan hydrogel--a step towards a scaffold for intervertebral disc tissue engineering. *European cells & materials* **2010**, *20*, 134-48; (i) Silva-Correia, J.; Miranda-Gonçalves, V.; Salgado, A. J.; Sousa, N.; Oliveira, J. M.; Reis, R. M.; Reis, R. L., Angiogenic Potential of Gellan-Gum-Based Hydrogels for Application in Nucleus Pulposus Regeneration: In Vivo Study. *Tissue Eng Pt A* **2012**, *18* (11-12), 1203-1212; (j) Pereira, D. R.; Silva-Correia, J.; Caridade, S. G.; Oliveira, J. T.; Sousa, R. A.; Salgado, A. J.; Oliveira, J. M.; Mano, J. F.; Sousa, N.; Reis, R. L., Development of Gellan Gum-Based Microparticles/Hydrogel Matrices for Application in the Intervertebral Disc Regeneration. *Tissue Engineering Part C: Methods* **2011**, *17* (10), 961-972; (k) Crevensten, G.; Walsh, A. J.; Ananthakrishnan, D.; Page, P.; Wahba, G. M.; Lotz, J. C.; Berven, S., Intervertebral disc cell therapy for regeneration: mesenchymal stem cell implantation in rat intervertebral discs. *Annals of biomedical engineering* **2004**, *32* (3), 430-4; (l) Su, W. Y.; Chen, Y. C.; Lin, F. H., Injectable oxidized hyaluronic acid/adipic acid dihydrazide hydrogel for nucleus pulposus regeneration. *Acta biomaterialia* **2010**, *6* (8), 3044-55; (m) Park, S.-H.; Cho, H.; Gil, E. S.; Mandal, B. B.; Min, B.-H.; Kaplan, D. L., Silk-Fibrin/Hyaluronic Acid Composite Gels for Nucleus Pulposus Tissue Regeneration. *Tissue Engineering. Part A* **2011**, *17* (23-24), 2999-3009; (n) Hu, J.; Chen, B.; Guo, F.; Du, J.; Gu, P.; Lin, X.; Yang, W.; Zhang, H.; Lu, M.; Huang, Y.; Xu, G., Injectable silk fibroin/polyurethane composite hydrogel for nucleus pulposus replacement. *Journal of Materials Science: Materials in Medicine* **2012**, *23* (3), 711-722.